



Publication Year	2021
Acceptance in OA	2025-03-14T11:10:37Z
Title	Mid-infrared reflectance spectroscopy of synthetic glass analogs for mercury surface studies
Authors	Morlok, Andreas, Renggli, Christian, Charlier, Bernard, Reitze, Maximilian P., Klemme, Stephan, Namur, Olivier, Sohn, Martin, Martin, Dayl, Weber, Iris, Stojic, Aleksandra N., Hiesinger, Harald, Joy, Katherine H., Wogelius, Roy, Tollan, Peter, CARLI, CRISTIAN, Bauch, Karin E., Helbert, Joern
Publisher's version (DOI)	10.1016/j.icarus.2021.114363
Handle	http://hdl.handle.net/20.500.12386/36792
Journal	ICARUS
Volume	361

Icarus

A Mid-Infrared Study of Synthetic Glass and Crystal Mixtures Analog to the Geochemical Terranes on Mercury --Manuscript Draft--

Manuscript Number:	
Article Type:	Research paper
Keywords:	Mercury, surface; Mineralogy; Infrared observations; Instrumentation; Spectroscopy
Corresponding Author:	Andreas Morlok Institut für Planetologie Münster, Germany
First Author:	Andreas Morlok
Order of Authors:	Andreas Morlok Christian Renggli, Ph.D. Bernard Charlier, Ph.D. Olivier Namur, Ph.D. Stephan Klemme, Professor Maximilian P. Reitze, Dr. Iris Weber, Dr. Aleksandra N. Stojic, Dr. Karin E. Bauch Harald Hiesinger, Professor Jörn Helbert, Dr.
Abstract:	The MERTIS (MErcury Radiometer and Thermal Infrared Spectrometer) onboard of the BepiColombo ESA/JAXA mission to Mercury will map the surface of Mercury in the wavelength range of 7-14 μm and for the interpretation of these spectra a database of analog materials is needed. We analysed bulk grain size fractions of a series of analog materials relevant to the distinct terranes of Mercury in diffuse reflectance in the mid-infrared (2.5 μm to 18 μm). Mineral mixtures cover a wide range of modal amounts of forsterite, enstatite, diopside and plagioclase, the resulting spectra can be divided into three distinct groups: (1) is dominated by a single glass feature, (2) by forsterite bands, and (3) by pyroxene bands. Despite often high contents, plagioclase features, are usually 'overprinted' by forsterite and pyroxene bands. Spectral parameter CF, an easy obtainable proxy for chemistry (SiO_2) and polymerization (SCFM) places the hermean mixtures mostly in the intermediate and basaltic range. The correlation of parameters easily obtainable in remote sensing, Mg/Si ratio, and CF, allows differing materials from high-energy evaporation processes in impacts from such formed in igneous processes. Preliminary comparison with a spectrum covering most of the hermean surface shows some similarity with band positions of the Inter Crater Plain and Heavily Cratered Terrains (IcP-HCT) and High-Mg Northern Volcanic Plains (High-Mg NVP) mixtures, but none of our spectra is able to reproduce the remote sensing data entirely.
Suggested Reviewers:	Patrick Peplowski, Ph.D. Johns Hopkins University Patrick.Peplowski@jhuapl.edu Involved in MESSENGER mission, background in instrumentation Karen Stockstill Cahill, Ph.D. Planetary Science Institute Karen.Stockstill-Cahill@jhuapl.edu Background in experimental petrology, infrared studies, and Mercury Alessandro Pisello, Ph.D.

	University of Perugia alessandro.pisello@unipg.it Works on glass and rocks in the mid-infrared
	Mehmet Yesiltas, Ph.D. Kirkklareli University myesiltas@knights.ucf.edu Background in mid-infrared studies of extraterrestrial materials
	Timothy D. Glotch, Professor Stony Brook University timothy.glotch@stonybrook.edu Background in spectroscopy of rocks and minerals for remote planetary sensing.
Opposed Reviewers:	

A Mid-Infrared Study of Synthetic Glass and Crystal Mixtures Analog to the Geochemical Terranes on Mercury

Andreas Morlok¹ (Corresponding Author; morlokan@uni-muenster.de; ++49 251 33424)

Christian Renggli²

Bernard Charlier³

Olivier Namur⁴

Stephan Klemme²

Maximilian P. Reitze¹

Iris Weber¹

Aleksandra N. Stojic¹

Karin E. Bauch¹

Harald Hiesinger¹

Joern Helbert⁵

¹Institut für Planetologie, Westfälische Wilhelms-Universität Universität Münster, Wilhelm-Klemm-Straße 10, 48149, Germany

²Institut für Mineralogie, Westfälische Wilhelms-Universität Universität Münster, Corrensstrasse 24, 48149 Münster

³University of Liege, Department of Geology, 4000 Sart-Tilman, Belgium

⁴Department of Earth and Environmental Sciences, KU Leuven, 3001 Leuven, Belgium

⁵Institute for Planetary Research, DLR, Rutherfordstrasse 2, 12489 Berlin, Germany

Abstract

The MERTIS (MErcury Radiometer and Thermal Infrared Spectrometer) onboard of the BepiColombo ESA/JAXA mission to Mercury will map the surface of Mercury in the wavelength range of 7-14 μm and the interpretation of these spectra a database of analog materials is needed. We analysed bulk grain size fractions of a series of analog materials relevant to the distinct terranes of Mercury in diffuse reflectance in the mid-infrared (2.5 μm to 18 μm). Mineral mixtures cover a wide range of modal amounts of forsterite, enstatite, diopside and plagioclase, the resulting spectra can be divided into three distinct groups: (1) is dominated by a single glass feature, (2) by forsterite bands, and (3) by pyroxene bands. Despite often high contents, plagioclase features, are usually 'overprinted' by forsterite and pyroxene bands.

Spectral parameter CF, an easy obtainable proxy for chemistry (SiO_2) and polymerization (SCFM) places the hermean mixtures mostly in the intermediate and basaltic range. The correlation of parameters easily obtainable in remote sensing, Mg/Si ratio, and CF, allows differing materials from high-energy evaporation processes in impacts from such formed in igneous processes.

Preliminary comparison with a spectrum covering most of the hermean surface shows some similarity with band positions of the Inter Crater Plain and Heavily Cratered Terrains (IcP-HCT) and High-Mg Northern Volcanic Plains (High-Mg NVP) mixtures, but none of our spectra is able to reproduce the remote sensing data entirely.

Key Words: Mercury, surface; Mineralogy; Infrared observations; Instrumentation; Spectroscopy

54

55 **1. Introduction**

56 The mid-infrared spectrometer MERTIS (MErcury Radiometer and Thermal Infrared Spectrometer) of
57 BepiColombo will map the surface of Mercury in the wavelength range of 7-14 μm , with a spatial
58 resolution of around 500 meters (Hiesinger et al., 2020). Spectral infrared features permit the direct
59 determination of Mercury's surface mineralogy (e.g., Rothery et al., 2020), which is not possible with
60 ground-based observations at this resolution (e.g., Sprague et al., 2009). In order to extract a more
61 accurate, as well as spatially-resolved mineralogy from the future spectral data, laboratory studies for
62 comparison with BepiColombo measurements are required to support spectral modelling. In order to
63 achieve this, the IRIS laboratory in Münster and the BED laboratory in Berlin were installed to
64 characterize a wide range of samples relevant to Mercury (e.g. Weber et al. 2018).

65 There are no known meteorites from Mercury (e.g., Weber et al., 2016). Hence, we rely on
66 remote sensing observations to study the mineralogy of Mercury. Multispectral imaging with the
67 Mercury Dual Imaging System (MDIS) and spectral reflectance measurements with the Mercury
68 Atmospheric and Surface Composition Spectrometer (MASCS) onboard MESSENGER recognized the
69 occurrence of graphite (Peplowski et al., 2016), sulphides (Vilas et al., 2016), and ice in polar regions
70 (Neumann et al. 2013). Spectral measurements also show that the crust of Mercury contains Fe^{2+} -poor
71 silicate minerals (Izenberg et al., 2014). However, spectral data from MESSENGER were insufficient to
72 identify the mineralogy of silicate phases and their abundances. Additionally, information on the
73 chemical composition of the hermean surface is based on data from X-ray, gamma-ray, and neutron
74 spectrometers onboard the MESSENGER spacecraft (e.g., Peplowski et al., 2011, 2016; Nittler et al.,
75 2020). Major element ratios obtained from the various instruments allowed the identification of several
76 chemically different regions (the so-called 'terranes') on the hermean surface. The terranes were named
77 the Low-Mg Northern Volcanic Plains (Low-Mg NVP), the High-Mg Northern Volcanic Plains (High-Mg

NVP), the Smooth Plains, the Inter Crater Plains and Heavily Cratered Terrains (IcP-HCT), and the High-Mg Province (Nittler et al., 2011; Peplowski et al., 2016; Weider et al., 2015; vander Kaaden et al., 2016; Peplowski and Stockstill-Cahill, 2019). Typical rock types on Mercury's surface can broadly be described as Fe-free and S-enriched komatiites, boninites, and andesites (e.g., Weider et al., 2015; Vander Kaaden et al., 2016; Peplowski and Stockstill-Cahill, 2019). Thermodynamic modeling and experimental petrology provide first order constraints on the mineralogy of such rocks, which are likely to be dominated by olivine, pyroxenes, plagioclase $\pm$ quartz, and (Mg,Ca)S sulfide (e.g., Charlier et al., 2013, Stockstill-Cahill et al., 2012; Namur & Charlier 2017; Vander Kaaden et al., 2017; Renggli et al., 2022). Data from mid-infrared spectroscopy from terrestrial telescopic observations integrating large surface regions also indicate a hermean mineralogy dominated by plagioclase and pyroxene (Donaldson-Hanna et al., 2007; Sprague et al., 1994, 2000, 2002, 2007; Sprague and Roush, 1998; Emery et al., 1998; Cooper et al., 2001).

In this study, we performed spectroscopic measurements in the mid-infrared wavelength range of analog glass and crystal mixtures relevant to Mercury's surface. The compositions of the glasses and crystals were chosen based on results from high-temperature crystallization experiments (1480-1100°C), that were equilibrated at crustal pressure (1 kbar) and reduced redox conditions (around IW-5; Namur and Charlier, 2017). The bulk compositions of these experiments are representative of the five main chemically distinct regions of the hermean surface introduced above, and the quenched products contain some of the following phases: silicate glass, plagioclase, forsterite, diopside, enstatite, quartz, FeSi metal, and sulfide (i.e., stoichiometric FeS). The samples we measured in this study are mixtures of pure endmember minerals and glass, very similar to the chemical compositions of the experimental products presented by Namur and Charlier, 2017. Synthetic glasses used in this study were previously described in detail in Morlok et al. (2021).

The overall aim of this study is to (a) provide mid-infrared reflectance spectra of hermean mineral/glass mixtures in different size fractions to allow granulometric studies, and under varying observational geometries to accommodate for changing observational conditions in orbit, and (b) provide first spectral parameters for the comparison with future data obtained by MERTIS.

ID	mineral / features	locality (origin)
13	Quartz	Mongolia
22	Diopside	Otter Lake, Quebec, Canada
28	Labradorite	Ihosy, Madagascar
53	Enstatite	Odegardens Verk, Bamble, Norway
249	Olivine	Dreiser Weiher, Germany

Table 1: Sources of natural crystalline phases used in this study. Samples are from larger, crushed single crystals and handpicked afterwards. Spectra can be found in Figure 2f. Chemical data see Table 3.

2. Samples and Techniques

2.1. Samples

Compositional and mineralogical characteristics of five terranes are covered in this study (Peplowski et al., 2015, Weider et al., 2015; Namur and Charlier, 2017; Denevi et al., Nittler et al., 2020). Large lava flows (~3.5 Ga) are typical of the Northern Volcanic Plains (Low-Mg and High-Mg NVP). The Low-Mg NVP is characterized by low Mg/Si ratios and a wider range of Al contents. This results in high-plagioclase abundance, together with diopside and forsterite, whereas the High-Mg NVP lavas contain a in comparison higher olivine abundance.

The intermediate Inter Crater Plain and Heavily Cratered Terrains (IcP-HCT), characterized by medium sized craters, show high Al contents, and contrasting low Mg. This resulted in high modal amounts of plagioclase.

3.5 to 3.9 Ga old Smooth plains cover ~40% of the hermean surface and are characterized by flat plains with numerous wrinkle ridges. The chemistry shows lower Mg/Si, S/Si, and Ca/Si ratios compared to the other regions, resulting in a mineralogy dominated by plagioclase, but minor mafic components. The old (4.2 – 4 Ga) High-Mg Province is characterized by high Mg/Si and Ca/Si, and low Al/Si ratios. The samples used in this study reflect a relatively low a a series of natural crystalline materials (Table 1). We selected a series of modal (wt%) phase compositions for each surface region identified in Namur and Charlier (2017) (Fig. 1). Chemical bulk compositions of the mixtures were calculated using the chemical composition of the starting materials and the individual weighed phase abundances (Table 2).

Detailed information about the minerals labradorite, enstatite, and forsterite (IDs 28, 53, 249) used in this study are given in Weber et al. (2021) and Reitze et al. (2021). ID 22 is a diopside, crushed to grain sizes from 25 μm – 250 μm which shows no sign of impurity. However, in the grain size fraction from 0 μm – 25 μm we observe signs (<5%) of serpentinization (van der Meer et al., 1995; Daly et al., 2011). However, this has only small impact on the overall bulk compositions of our samples because we used low proportions of ID 22 Diopside in the mixtures.



The mineral samples are natural terrestrial materials. While the chemical composition of these minerals is, overall, similar to minerals on Mercury, these phases formed in vastly different environments. In particular, terrestrial magmatism is much more oxidized than expected for Mercury, with the latter of which is characterized by redox conditions buffered by the iron-wüstite buffer (IW-7 to IW-3), whereas magmatism on the Earth usually happens at redox conditions between IW-2 to IW+8 (McCubbin et al., 2012; Namur et al., 2016a,b; Cartier and Wood, 2019). As a result, for example different $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratios in olivine and pyroxene can be expected.

Silicate glasses were synthesized to represent the amorphous component in our mixtures. Details on the synthesis protocol can be found in Morlok et al. (2021). We produced a series of six synthetic glasses using reagent grade oxides as starting materials. Melts were kept in a gas mixing furnace for 6 h at 1450°C at the graphite-CO buffer (IW-6.7). The glasses cover the observed compositional range of the terranes (e.g., 1.6 wt% - 19.0 wt% MgO).

Size fractions for each mixture were mixed separately (<25 µm, 25 µm – 63 µm, 63 µm -125 µm, 125 µm -250 µm). This results in minor divergences from the modal starting compositions based on the laboratory experiments (see Table 2). The finest fraction (<25 µm) was chosen to represent the regolith grain size, which exhibits the important Transparency Feature (TF), a characteristic reflectance low. The other size fractions were selected to cover intensity changes related with grain sizes. Increasing grain size is correlated with increasing intensity (e.g., Salisbury, 1993; Mustard and Hayes, 1997).

For measurements, the samples were filled into aluminum sample cups, and the surface flattened with a spatula (see Mustard and Hayes, 1997 for details).

Figure 1: Overview of the modal composition of the selected samples (Namur and Olivier, 2017). (a) pyroxene, plagioclase, and forsterite, (b) pyroxene, forsterite, and glass. All in wt%.

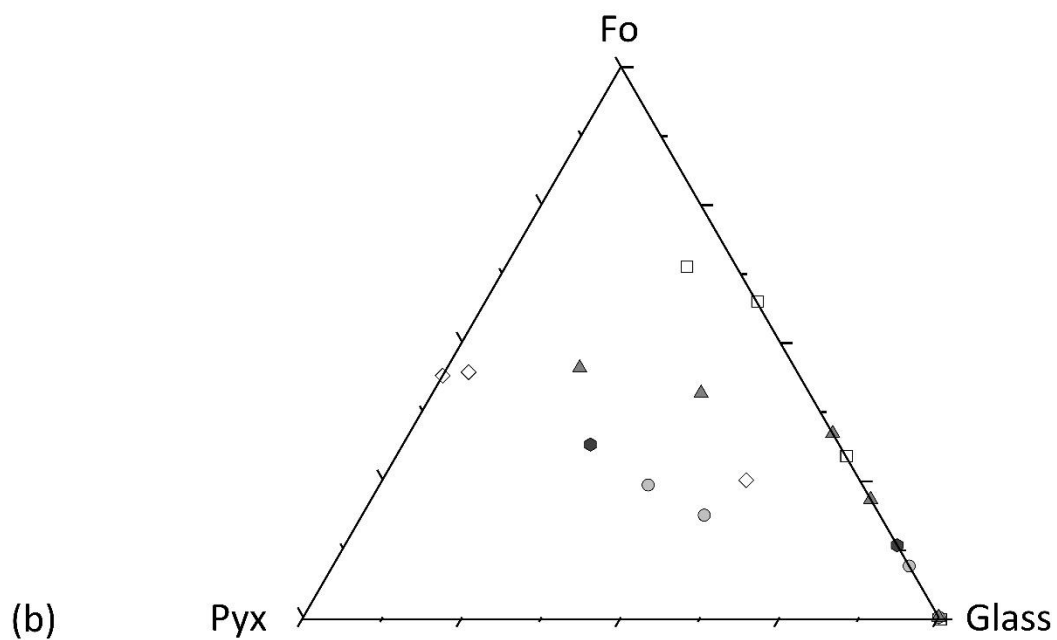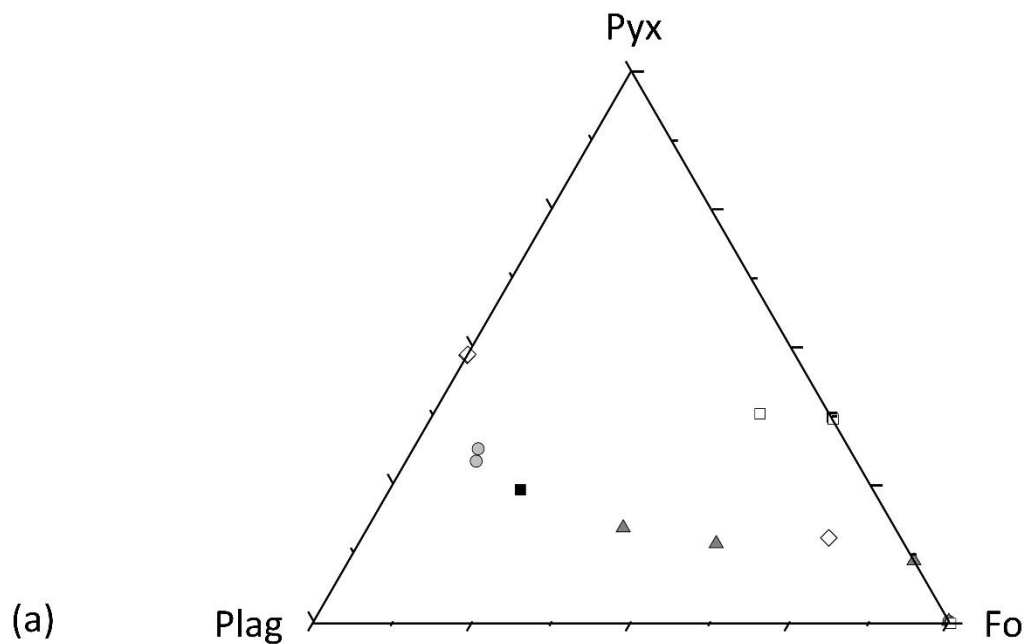

- Smooth Plains (SP)
- High-Magnesium Province (High-Mg Province)
- ▲ Inter-Crater Plain and Heavily Cratered Plains (ICP-HcT)
- ◇ High Magnesium Northern Volcanic Plains (High-Mg NVP)
- Low Magnesium Northern Volcanic Plains (Low-Mg NVP)

Figure 1

2.2. Infrared Studies

We used a Bruker Vertex 70v infrared spectrometer with a liquid nitrogen cooled MCT (HgCdTe) detector at the IRIS laboratory in Münster. Analyses were made in the wavelength region of 2.5 μm to 18 μm in low vacuum (100 Pa). For each spectrum, 512 scans were accumulated at a spectral resolution of 4 cm^{-1} (20 nm at 7 μm , 80 nm at 14 μm). This spectral resolution is comparable to MERTIS onboard BepiColombo (e.g., 90 nm, Hiesinger et al. 2010 and 2020). For calibration, the instrument background was eliminated by ratioing the sample spectra against the spectrum of a diffuse gold standard (INFRAGOLD™) measured under the same conditions. Analyses were made at 13° incidence (i) and 13° emergence (e), 20° (i)/30°(e), and 30°(i)/30°(e) in order to simulate observational geometries of an orbiter. The results presented in the main text were made at 20°(i) and 30°(e), results for the other settings are available in the supplement. The results are presented in reflectance from 6 μm – 18 μm (Fig. 2a-e), which covers the range of the MERTIS instrument (7 μm – 14 μm) but omits volatile features. It also includes the Christensen Feature (CF, the Reststrahlenbands RB; the molecular vibration modes of the materials), and the Transparency Feature (TF; typical for the finest <25 μm size fractions). Since the aim of our study is to compare the laboratory data with future remote sensing data, measurements from the laboratory have to be recalculated from reflectance to emissivity using Kirchhoff's law: $\epsilon = 1 - R$ (R = Reflectance, ϵ = Emission, Nicodemus, 1965). However, a prerequisite for the validity of Kirchhoff's law is that the reflected light should be collected in all directions. In an ideal case directional emissivity and directional hemispherical reflectance should be compared. However, we used a bi-directional setup. Earlier studies showed that this approach mainly affects the reflectance intensity, but not band positions. This must however be kept in mind when comparing the results in a quantitative manner with emission data (Salisbury et al., 1991; Hapke, 1993; Thomson and Salisbury, 1993; Salisbury et al., 1994; Christensen et al., 2001). The spectra presented in this study are accessible on our online database at the Institut für Planetologie in Münster (<http://bc-mertis-pi.uni-muenster.de/>).

	Low-Mg NVP		High-Mg NVP		Smooth Plains		IcP- HCT					
	ID 349 (Y131)	ID 350 (Y172)	ID 355 (Y133)	ID 356 (Y143)	ID 357 (Y144)	ID 345 (Y140)	ID 344 (Y143)	ID 343 (Y144)	ID 351 (Y126)	ID 352 (Y131)	ID 353 (Y132)	ID 354 (Y146)
	—	— _P										
Glass	86.9	29.5	96.8	42.0	30.2	90.7	53.8	42.3	78.6	66.6	42.3	20.6
Forsterite	8.2	14.3	3.2	12	10.7	9.3	5.1	5.9	21.4	29.7	32.5	31.5
Diopside	4.9	17.1		9.1	12.1		2.2	10.7		3.7	8.1	8.3
Enstatite				16.0	20.3		11.3	7.4				5.0
Plagioclase		39.1		20.8	26.6		27.6	33.7			17.1	33.4
Quartz												1.2
SiO ₂	64.52	59.35	58.71	59.01	60.41	62.10	61.34	59.76	54.85	59.00	55.73	55.72
TiO ₂	0.20	0.09	0.40	0.11	0.10	0.42	0.13	0.11	0.28	0.16	0.11	0.07
Al ₂ O ₃	13.42	15.40	10.61	12.34	12.04	12.97	16.02	15.96	12.98	10.29	11.31	12.47
Cr ₂ O ₃	0.00	0.01	0.00	0.01	0.01	0.00	0.01	0.01	0.01	0.01	0.02	0.02
FeO	0.97	1.79	0.32	2.80	3.20	0.82	1.63	1.56	1.89	2.70	3.03	3.42
MnO	0.10	0.06	0.17	0.07	0.05	0.16	0.07	0.07	0.08	0.10	0.09	0.06
MgO	9.03	10.57	19.99	14.86	14.68	12.83	9.20	9.22	20.56	18.74	19.78	19.28
CaO	6.25	8.89	6.94	6.91	6.41	6.18	6.53	8.63	5.64	4.79	6.27	5.95
Na ₂ O	5.22	3.92	3.19	3.64	3.29	4.36	4.70	4.34	3.84	4.01	3.46	3.06
K ₂ O	0.20	0.23	0.10	0.17	0.19	0.18	0.21	0.21	0.11	0.16	0.15	0.18
Total	99.91	100.31	100.43	99.93	100.39	100.02	99.85	99.86	100.24	99.97	99.94	100.24
	High-Mg Prov.		Crystal line						Glass			
	ID 348 (Y126)	ID 347 (Y131)	ID 346 (Y146)	ID 249 Forsterite	ID 22 Diopside	ID 53 Enstatite	ID 28 Plagioclase	ID 13 Quartz	ID 339	ID 338	ID 181	ID 174
Glass	70.5	42.5	27.7						100	100	100	100
Forsterite	29.5	36.2	35.8	100								
Diopside		21.2	25.3		100							
Enstatite			1.3			100						
Plagioclase			7.7				100					
Quartz			2.0					100				
SiO ₂	53.87	55.14	56.74	40.96	55.08	57.48	55.63	101.42	58.62	55.90	59.29	64.26
TiO ₂	0.30	0.11	0.09	0.02	0.05	0.04	0.01	0.01	0.35	0.41	0.41	0.46
Al ₂ O ₃	7.73	6.63	6.41	0.04	0.31	0.14	27.87	0.01	16.49	7.31	10.95	14.30
Cr ₂ O ₃	0.01	0.02	0.02	0.04	0.01	0.01	0.02	0.01	0.00	0.00	0.00	0.00
FeO	2.51	3.67	3.90	8.38	2.63	9.09	0.10	0.01	0.13	0.10	0.05	0.05
MnO	0.16	0.11	0.09	0.11	0.14	0.04	0.01	0.01	0.08	0.25	0.17	0.16
MgO	28.30	23.87	23.25	50.50	16.80	33.16	0.01	0.00	12.43	26.94	19.00	8.97
CaO	5.07	7.82	7.71	0.09	25.10	0.21	10.32	0.00	7.15	7.15	7.16	6.81
Na ₂ O	2.33	2.59	2.16	0.01	0.19	0.02	5.29	0.01	4.88	2.95	3.29	4.81
K ₂ O	0.08	0.10	0.13	0.00	0.01	0.01	0.31	0.01	0.14	0.11	0.11	0.19
Total	100.35	100.06	100.51	100.14	100.30	100.21	99.57	101.50	100.27	101.11	100.44	100.01
				Fo#91	En#46 Wo#50	En#86	An#51					

Table 2. Chemical bulk compositions (wt. %) and modal mixtures used in this study. Bulk chemical compositions of the mixtures used in this study (in wt.%) were calculated using the chemical compositions of the components and the modal compositions. ID + Number: Sample ID used in the IRIS database (see 2.2. Infrared Studies). Name of sample based on starting composition used following Namur and Charlier (2017). Fo#: Forsterite content, En#: Enstatite content, An#: Anorthite content, Wo#: Wollastonite content (mol.%).

3. Results

Most samples show spectral features at wavelengths shorter than 7 μm , usually at 2.7 μm – 3.0 μm , 3.4 μm – 4 μm , and 5 μm – 7 μm . These are volatile features due to adsorption and absorption of terrestrial water and unavoidable minor contaminations of the terrestrial minerals used for the mixtures.

3.1. Low-Mg Northern Volcanic Plains

The glassy end member is represented by low Mg sample ID 174 (Morlok et al., 2021), and has the CF at 7.9 μm , the TF at 11.8 μm , and a single RB at 9.6 μm . The spectrum of ID 350 has the CF between 7.8 μm and 8.1 μm , with several pyroxene RB at 9.4 μm , 9.9 μm , 10.2 μm , 10.5 μm – 10.6 μm and 10.8 μm . The TF is located at 11.3 μm – 11.5 μm (Tab.4; Fig.2a, f). The dominance of the glassy component results in a simpler spectrum with few bands for ID 349: the CF is at 7.8 μm - 7.9 μm , the TF at 11.6 μm . The strongest olivine RB is at 9.4 μm -9.5 μm , with minor features at 10.2 μm and 10.5 μm - 10.6 μm (Tab.4; Fig.2a, f).

3.2. High-Mg NVP

The glass-rich samples ID 355 and pure glass ID 181 have the CF at 8 μm to 8.1 μm and the TF at 11.9 μm . They have a strong RB at 9.7 μm to 9.8 μm , ID 355 also has weak olivine bands at 10.5 μm . Crystal-bearing ID 356 and ID 357 show similar pyroxene band positions, although they are different in intensities and band shapes. Their CF is between 7.8 μm and 8.2 μm (Table 4; Fig. 2b, f). Common pyroxene RBs are at 9.4 μm -9.5 μm , 10.2 μm , 10.5 μm , 10.8 μm , and 11.3 μm . At longer wavelengths, bands occur at 14.4 μm -14.5 μm , and 15.6 -15.8 μm . The TF is located at 11.4 μm .

3.3 Intra Crater Plains - Heavily Cratered Terrane (IcP-HCT)

The glass endmember, represented by high-Mg glass ID 181 (Morlok et al., 2021) has the CF at 8 μm to 8.1 μm , the TF at 11.9 μm , and a single RB at 9.8 μm . Similar to the High-Mg Province, the spectra of the IcP-HCT region (ID 351, ID 352, ID 353, ID 354) are dominated by olivine features, reflecting the forsterite modes ranging from 21 to 33 wt% (Table 4; Fig. 2c, f). The CF is located between 7.8 μm and 8.2 μm . The strongest RBs are at 9.4 μm - 9.7 μm , 10.2 μm , 10.5 μm -10.6 μm , and 11.9 μm . The TF is again a broad feature without distinct maximum. A dip at 7 μm is observed for diopside-rich samples ID 353 and ID 354.

3.4. Smooth Plains

Glass-dominated mixture ID 345 has a CF range from 7.9 to 8 μm , with an RB at 9.6 μm , 10.2 μm and 10.5-10.6 μm . The TF is located at 11.8 μm .

The-Smooth Plains samples ID 343 and ID 344 show generally similar pyroxene band positions (Table 4; Fig. 2d, f) reflecting their similar bulk composition, but with ID 344 having more pronounced, 'sharper' bands. The CF is between 7.8 μm and 8 μm for ID 343, and between 7.8 μm and 7.9 μm for ID 344. Significant RBs are between 9.4 μm and 9.6 μm and at 9.9 μm , 10.2 μm , 10.5 μm , 10.8 μm and 11.4 μm .

The TF is located at 11.7 μm . Various minor spectral features are found at longer wavelengths, mainly from 15.5 μm to 15.8 μm . The diopside-rich sample ID 343 shows a dip at 6.9 μm to 7 μm (or a small feature at 7.3 μm) in the finest grain size fraction.

3.5. High-Mg Province

The glassy end member ID 338 has the CF at 8.2 μm , TF at 12.1 μm and the dominating RB at 9.9 μm . As a result of the high forsterite contents (30-36 wt%), spectra of mixtures ID 346, ID347, and ID348 are quite similar (Table 2; Fig. 2e, f). The plagioclase and pyroxene contents show no significant bands in the spectra. The CF ranges from 7.8 μm to 8.6 μm , and the strongest RB is at 10.6 μm . Further common bands are found at 10.2 μm and 11.9 μm – 12 μm . ID 346 and ID 347 share further RBs at 9.4 μm and 10.8 μm . The TF is a broad feature without a clear peak. Features at longer wavelengths are seen between 15.8 μm and 16 μm . Samples ID 346 and ID 347 shows a dip at 6.9 μm in the finest grain size fractions.

Figure 2a-f: Mid-infrared reflectance spectra of the grain size fractions. Black: 125 - 250 μm , dark grey: 63 – 125 μm , grey: 25 - 63 μm , light grey: 0-25 μm . Gl: glass, Fo: forsterite, Di: diopside, Pl: plagioclase, En: enstatite, Qz: quartz. Vertical green lines: 249 forsterite bands, vertical yellow lines: pyroxene features (see Figure 3).

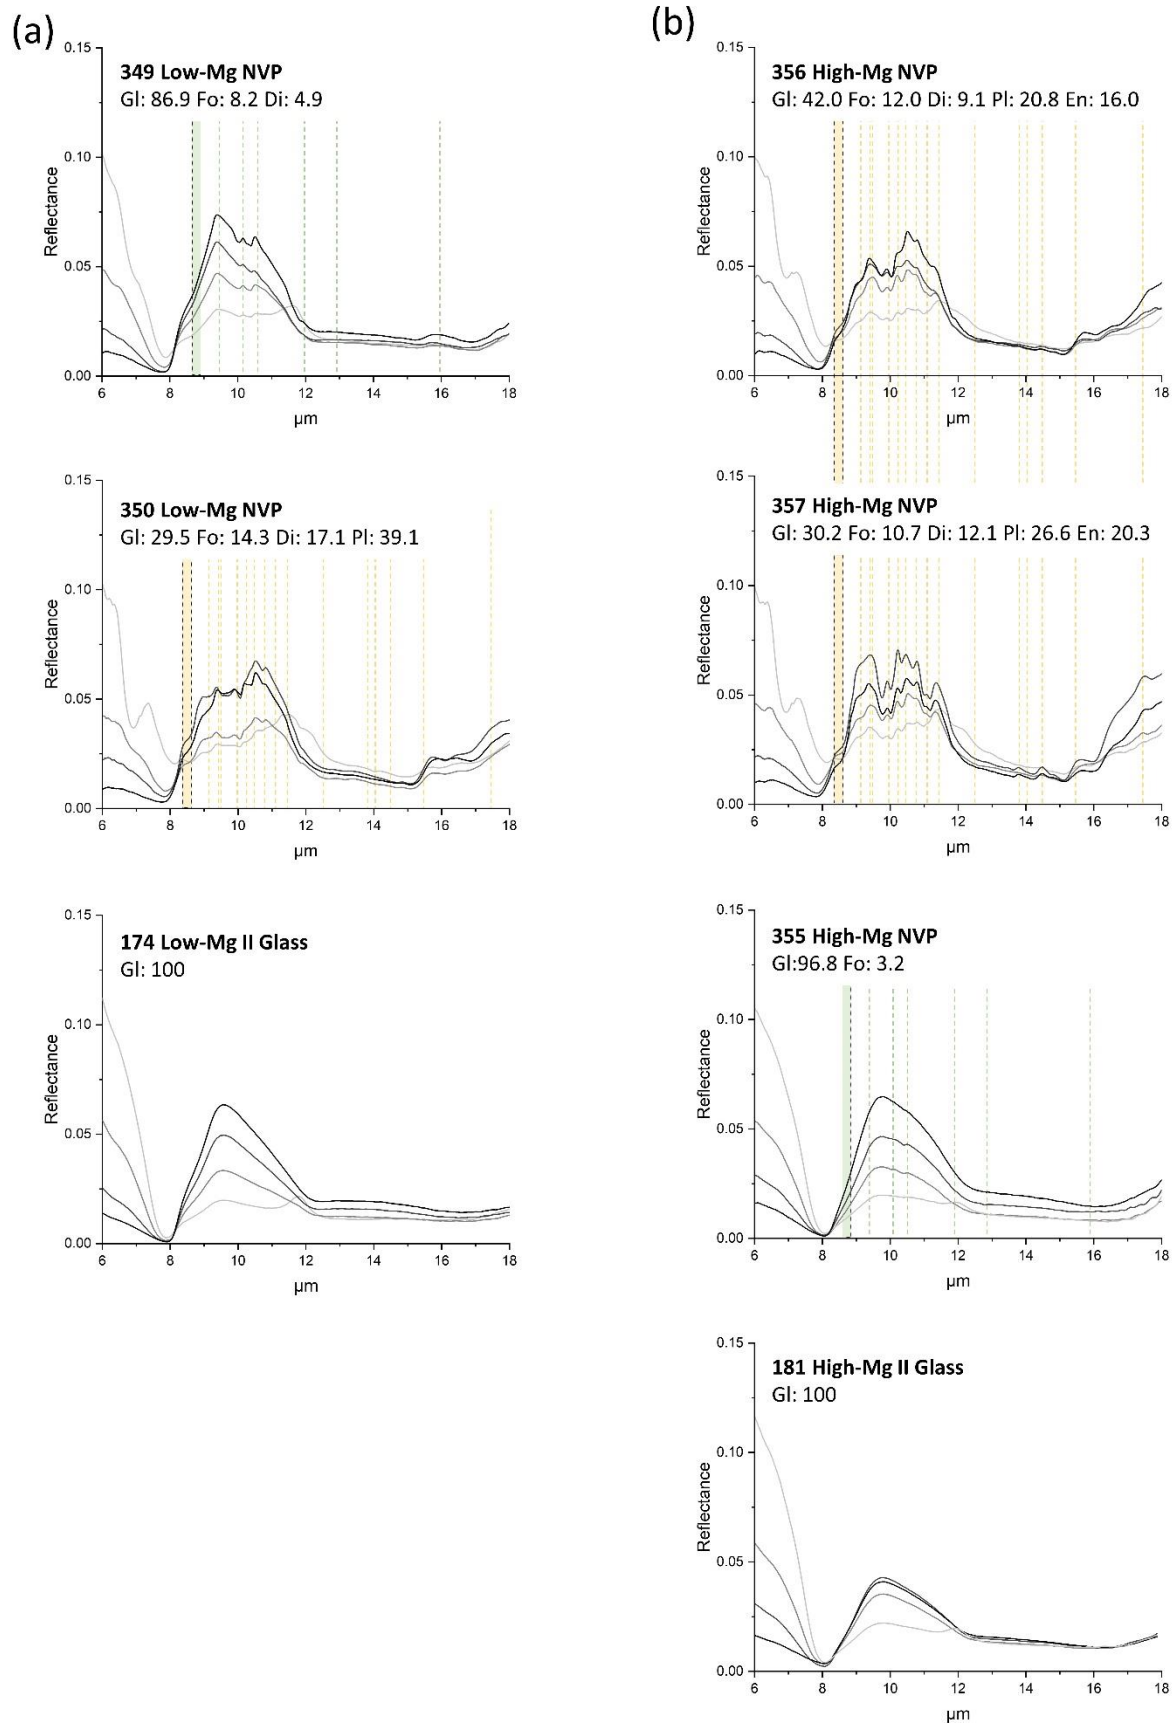


Figure 2

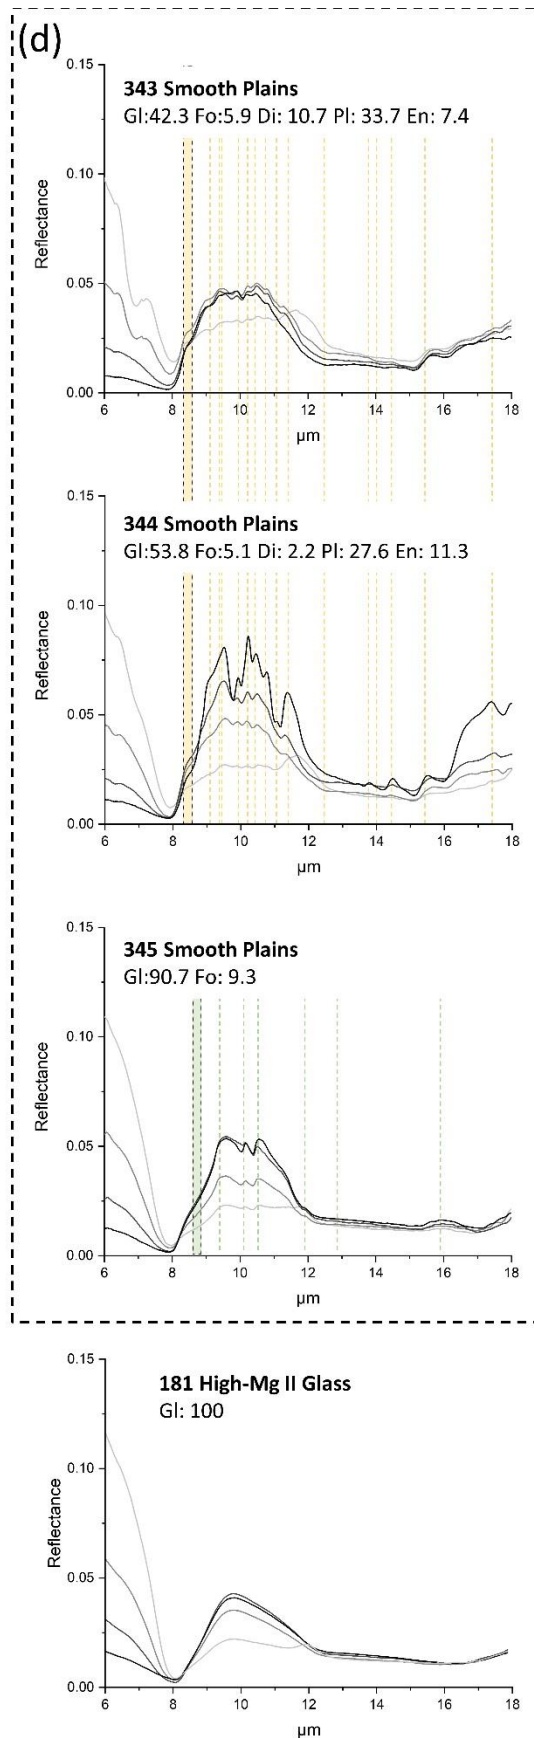
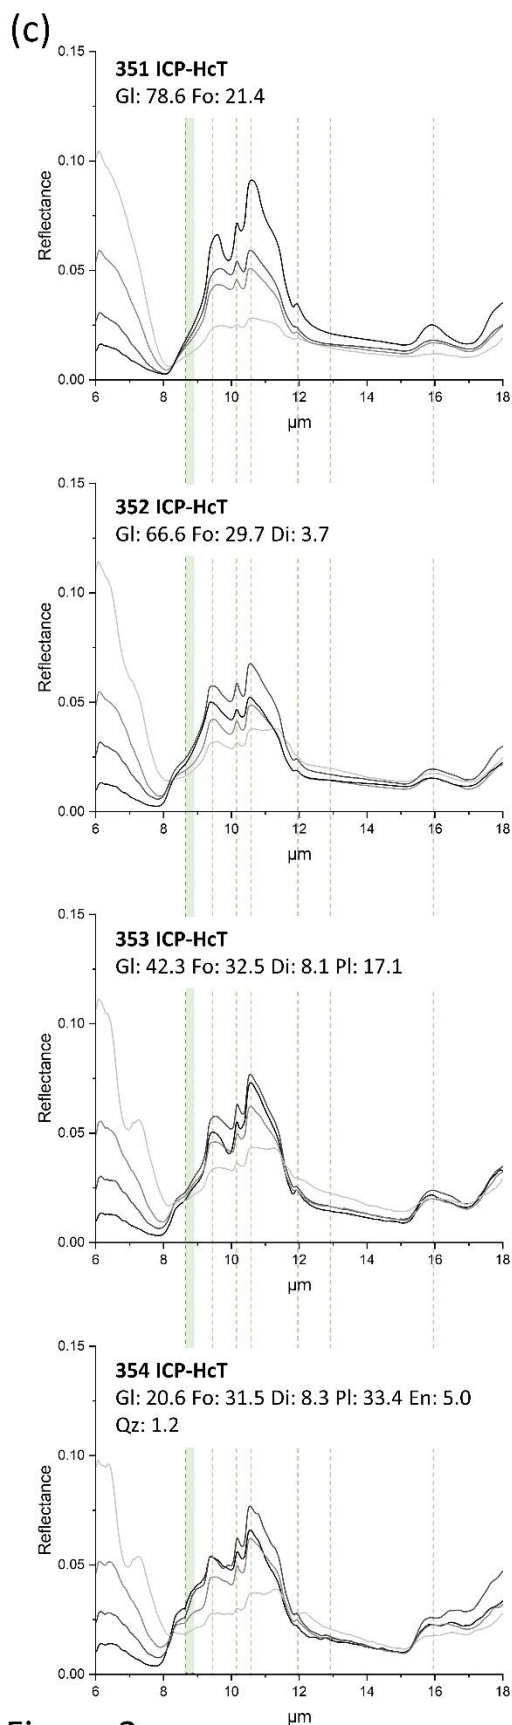


Figure 2

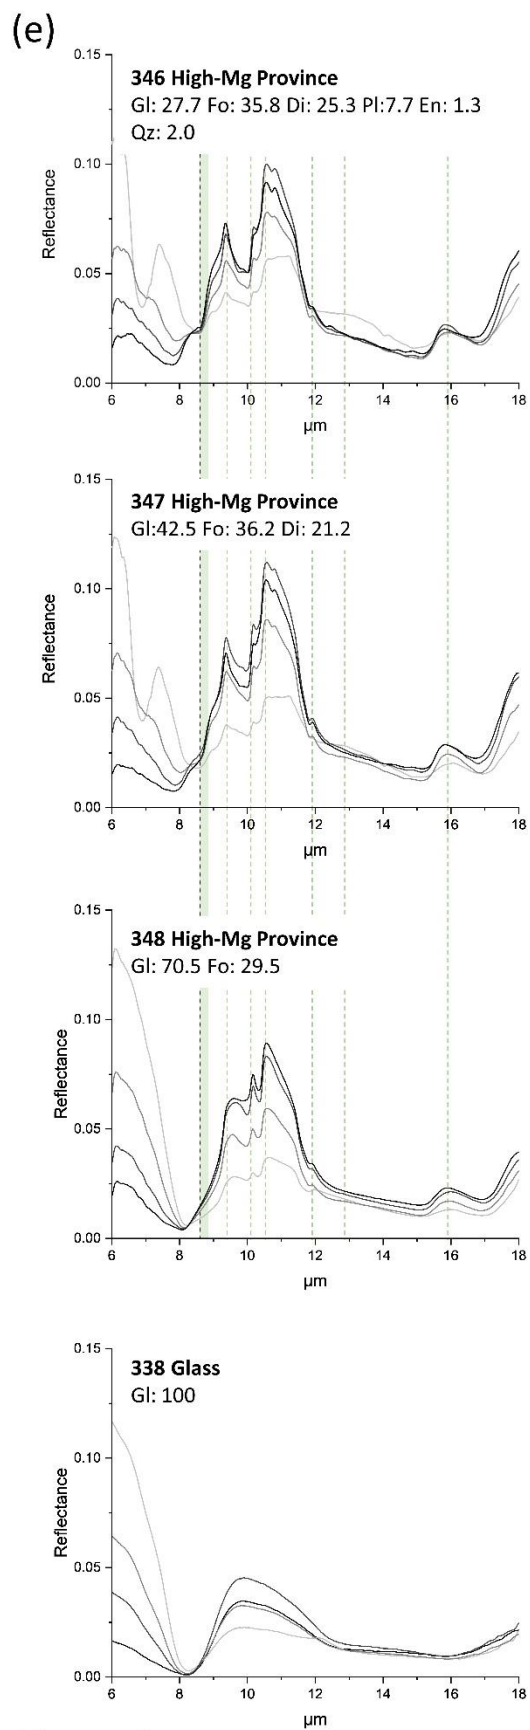


Figure 2

(f)

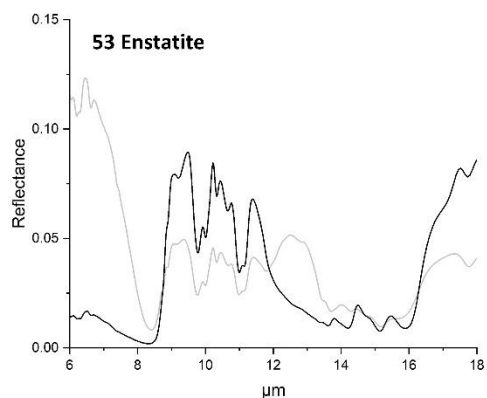
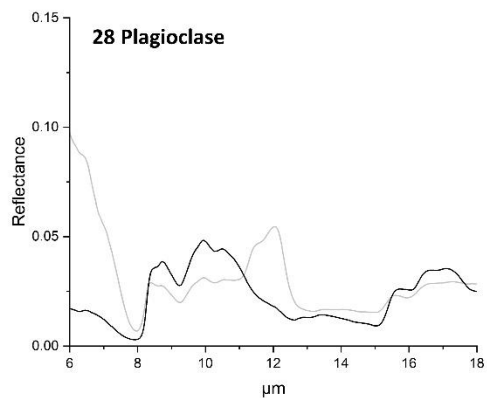
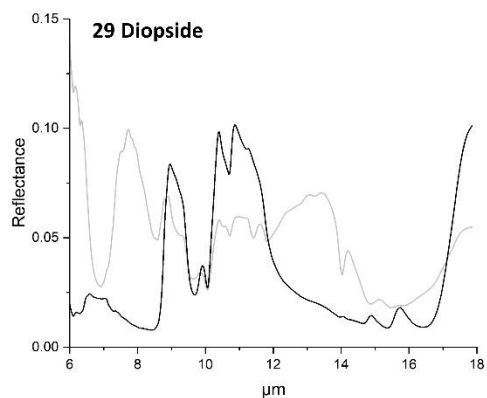
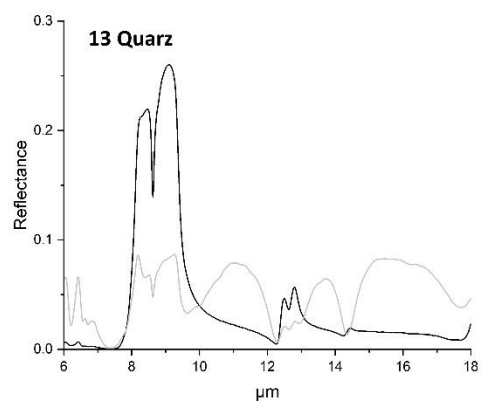
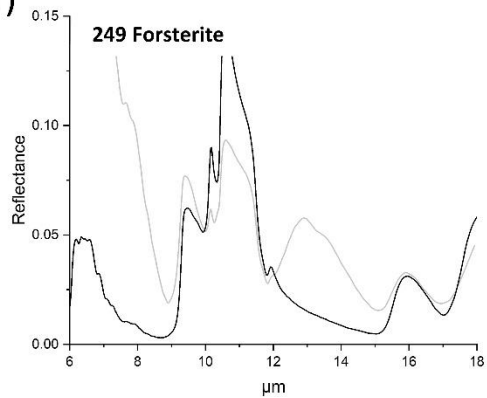


Figure 2

4. Discussion

4.1. Interpreting the mixtures

Despite the often-complex mixtures of up to five crystalline and one amorphous phase, the resulting spectra of the mixtures can be divided into three groups (Table 3). The simplest spectra are dominated by glass, demonstrated by prominent RB from 7.9 μm – 8.3 μm . Besides the ‘pure’ glassy end members (ID 174, ID181, and ID 338), sample ID 355 High-Mg NVP with only minor (3 wt%) crystalline content shows barely any recognizable additional bands (Fig. 2b). In the second group, forsterite features tend to dominate (Table 3): bands near 9.4 μm to 9.5 μm , 10.2 μm , 10.6 μm , 11.9 μm , and 15.9 μm -16 μm (Fig.2c, e). In the finest size fraction (< 25 μm), the TF the 10.6 μm band is turned into a broader feature with another peak at 11.2 μm to 11.3 μm .

A third group exhibits the pyroxene RB features of diopside and enstatite near 8.9 μm to 9.1 μm , 9.4 μm - 9.5 μm , 9.9 μm , 10.2 μm , 10.4 μm - 10.8 μm , 11 μm - 11.1 μm - 11.3 μm , and 11.4 μm to 11.6 μm (Fig.2a-e). The finest grain size fractions of diopside-rich samples also show a dip at 6.9 μm to 7 μm , which is also prominent in the finest grain size fraction of the ID 22 diopside bulk material.

Although plagioclase feldspar is often a dominant component in the mixtures, its RB features tend to be subdued by the forsterite and enstatite bands. The only RB, which is visible in all samples with a high amount of plagioclase is its RB 1 as a shoulder at around 8.3 μm (e.g. 356 and 357 High-Mg NVP; Fig. 4b). This is probably caused by its flat spectrum, that is dominated by a broad RB at 8.7 μm , and particular at 9.9 μm to 10 μm and 10.5 μm to 10.6 μm , which are superimposed by the more pronounced pyroxene and olivine bands. However, further hints of significant plagioclase contents are higher intensities in the $\approx$ 10 μm to 10.5 μm range due to the strong plagioclase double-feature, which provides a generally broad feature, which serves as some kind of underlying continuum, as observed in samples ID 350 and ID 356 (Fig.2a, b). In the wavelength range around 12 μm glasses and plagioclases have overlapping TF. In earlier experiments using plagioclase (ID28) with varying degrees of Al-Si order (Reitze et al. 2021a) plagioclases with low degree of Al-Si order show a single TF, such with a higher order a double peak or

peak with shoulder, as seen in the case of the plagioclase ID28 used in this study (e.g. 350 Low-Mg NVP or 357 High-Mg NVP; Fig.2a, b).

The quartz content is too low (few wt%) to produce any recognizable RB (e.g., 2 wt.% in ID 346, 1.2 wt.% in ID 354; Fig.4b and e). This raises the question of the ‘critical’ concentration (i.e. detection limit) of a phase to be recognizable in a mixture. In simple mixtures of glass and a crystalline phase, minute contents of 3 wt.% olivine in ID 355 High-Mg NVP(Fig.2b) provide just enough signal to identify the mineral with features at 10.5 μm and 11.9 μm (Table 4). Contents of 9.3 wt% olivine in ID 345 Smooth Plains (Fig.2d) are easily recognizable with bands at 9.6 μm , 10.2 μm , 10.6 μm , and 11.4 μm (Table 4). However, two minor components of 8.2 wt.% olivine and 4.2 wt.% diopside in ID 349 Low-Mg NVP (Fig.4a) only allow the clear identification of the olivine 9.4-9.5 μm , 10.2 μm , 10.5 μm -10.6 μm , and 11.6 μm . Increasing number of phases will make the identification of a minute phase in the crowded range around 10 μm difficult. For the semi-quantitative identification of further components, rationing of spectral parameters could provide an alternative.

	RB Features	Samples
ID 338, 181,174 Glass	9.6 - 9.9 μm	ID 174, ID181, ID 338,
ID 249 Forsterite	9.4 μm - 9.5 μm , 10.2 μm , 10.6 μm , 11.9 μm , 15.9 μm -16 μm	ID 355 High-Mg NVP ID 349 Low-Mg NVP, ID 346, 347, 348 High-Mg Prov., ID 351, 352 353, 354 IcP-HCT, ID 345 Smooth Plains, ID 355 High-Mg NVP
ID53 Enstatite/ 29 Diopside	8.9 μm - 9.1 μm , 9.4 μm - 9.5 μm , 9.9 μm , 10.2 μm , 10.4 μm -10.8 μm , 11 μm -11.1 μm - 11.3 μm , 11.4 μm to 11.6 μm	ID 350 Low-Mg NVP, ID 343, 344 Smooth Plains, ID 356, 357 High-Mg NVP

Table 3. Overview of the groups into which the mixture spectra can be divided based on their dominant features.


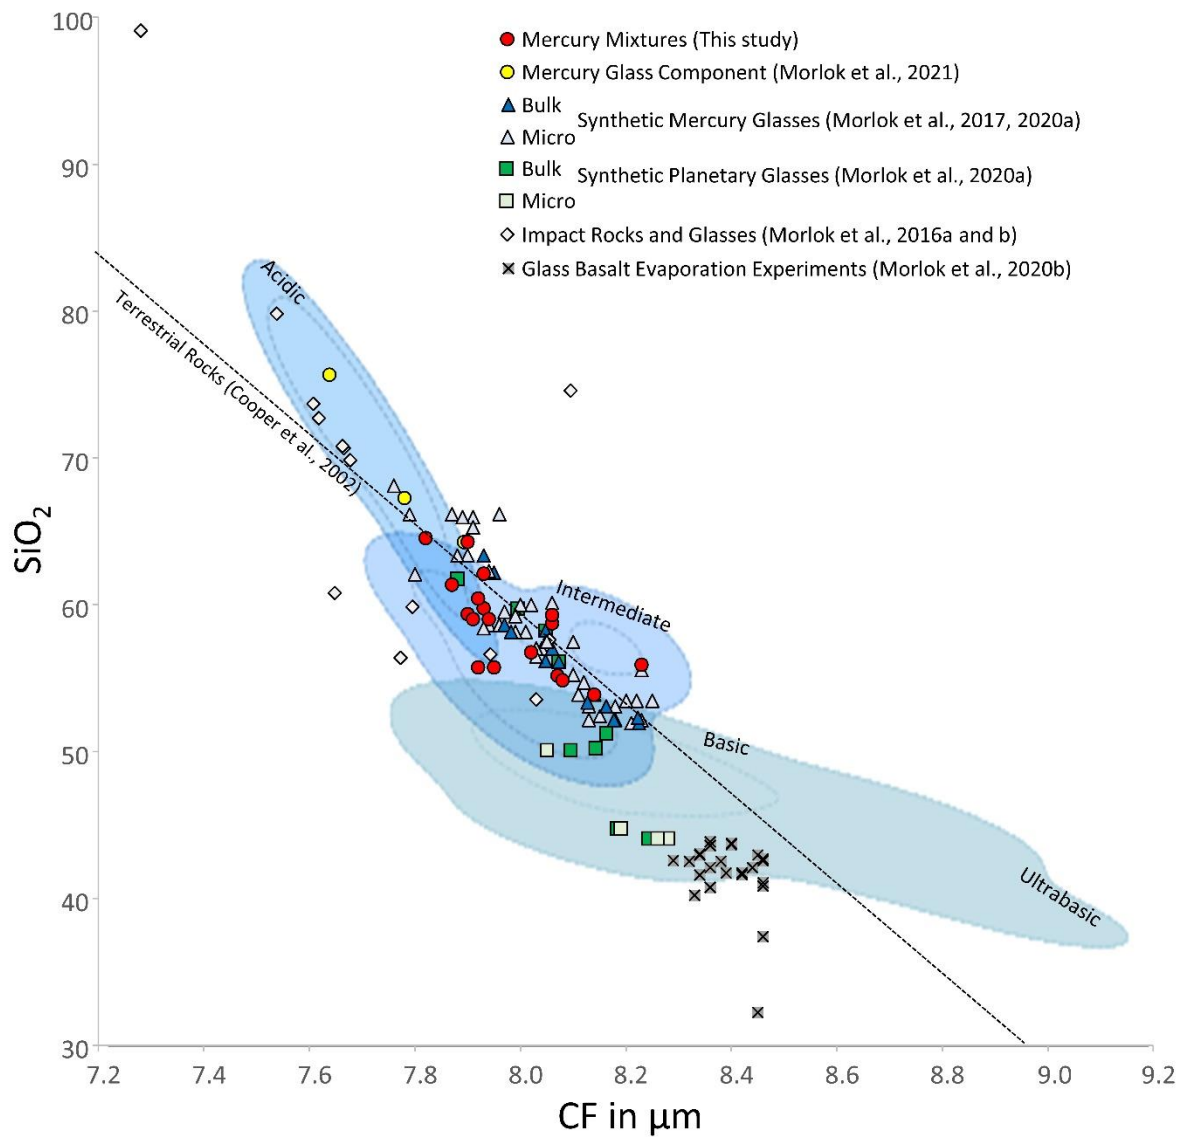


Figure 3a

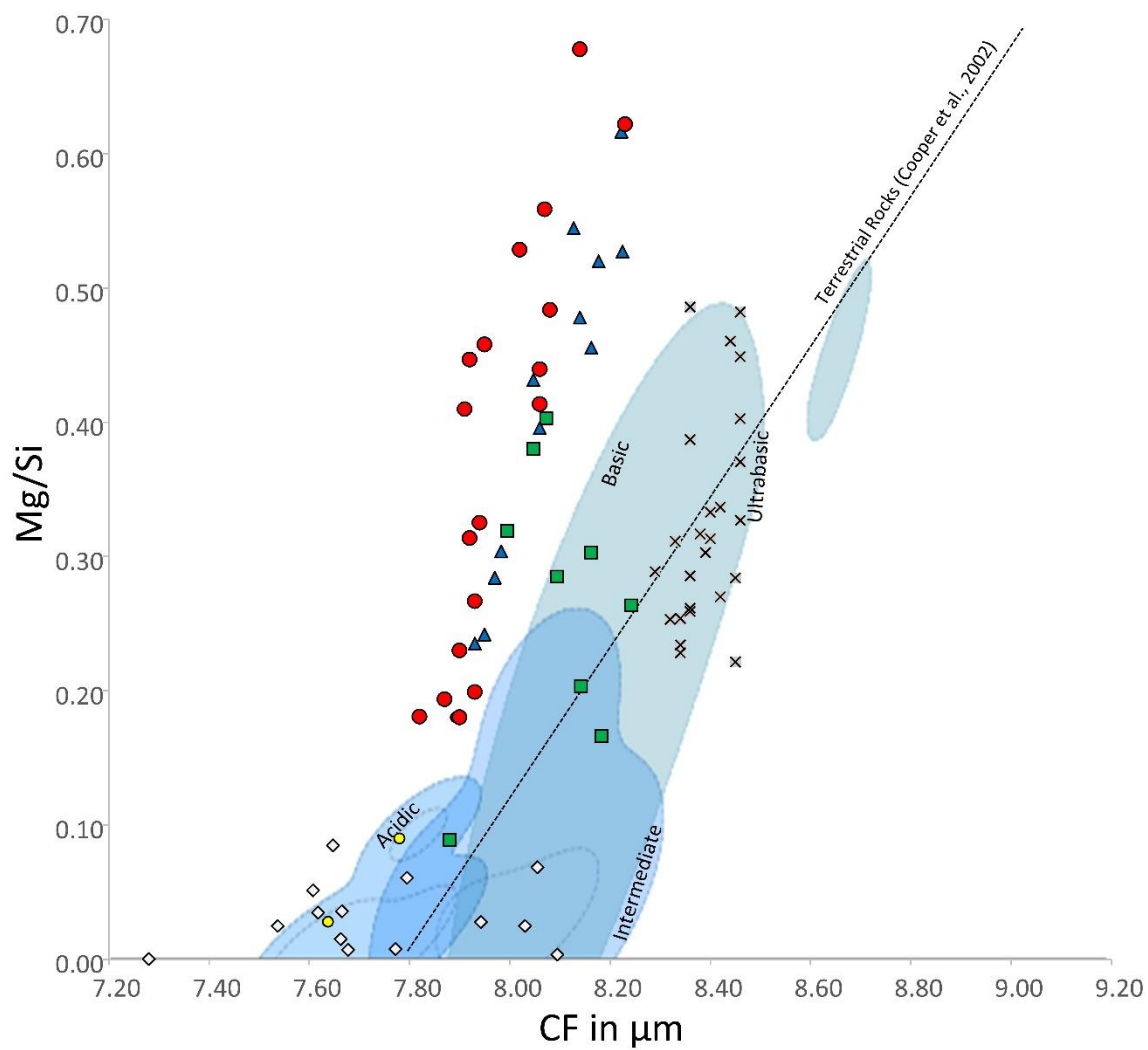

- Mercury Mixtures (This study)
- Mercury Glass Component (Morlok et al., 2021)
- ▲ Bulk Synthetic Mercury Glasses (Morlok et al., 2017, 2020a)
- △ Micro Synthetic Mercury Glasses (Morlok et al., 2017, 2020a)
- Bulk Synthetic Planetary Glasses (Morlok et al., 2020a)
- Micro Synthetic Planetary Glasses (Morlok et al., 2020a)
- ◇ Impact Rocks and Glasses (Morlok et al., 2016a and b)
- ✕ Glass Basalt Evaporation Experiments (Morlok et al., 2020b)

Figure 3b

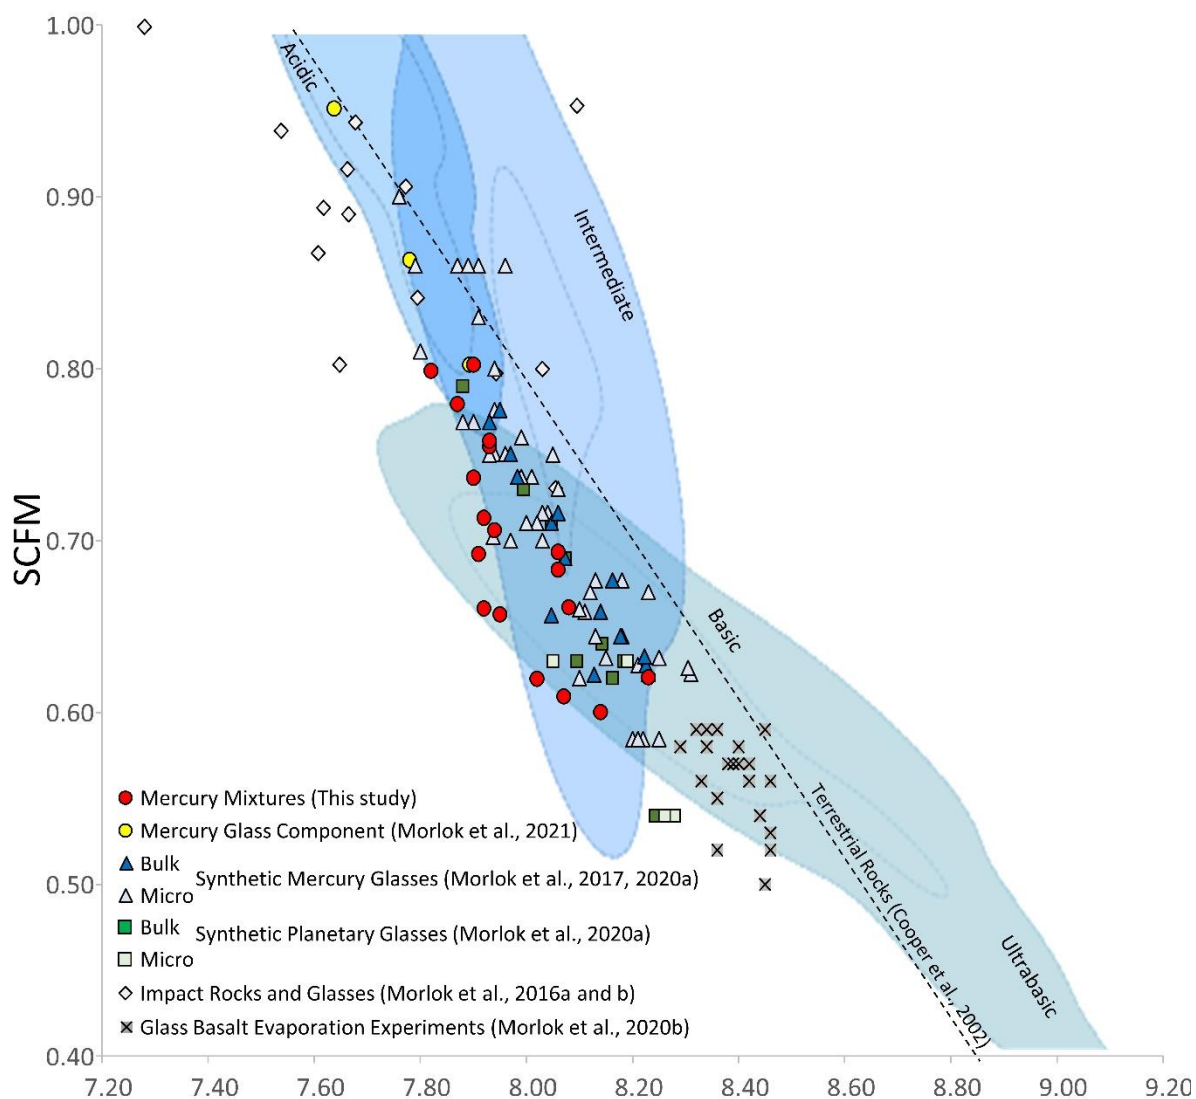


Figure 3c

Figure 3. (a) Correlation of SiO₂ abundance with CF position. Results from this study (red circles) mainly fall into the intermediate area. **(b)** Comparison of the Mg/Si ratio with the CF. The refractory glasses produced with laser-heating (Morlok et al., 2020b) is easy to distinguish from the samples with hermean and planetary compositions. **(c)** Comparison of SCFM (SiO₂, CaO, FeO, MgO) index of polymerization to CF position. Blue shaded areas and dashed line mark are from Cooper et al. (2002) for terrestrial rocks.

4.2 Correlation of Bulk Composition with Spectral Parameters

Christiansen Feature and SiO₂

The CF can be extracted even from ‘noisy’ spectra. Hence any correlation of the CF with other features will help to derive basic information about composition and mineralogy from remote sensing data. A classical method to correlate the average CF of all grain size fractions with chemical composition is the comparison of the SiO₂ content (wt.%) with the CF (Cooper et al., 2002). The comparison of the hermean mixtures in this study with earlier results (Fig.3a) shows that most of the mixtures fall close to the correlation line for terrestrial materials, which is the best fit for results of a range of terrestrial rocks scattering a bit due to compositional variances as indicated by the blue shaded areas (Cooper et al., 2002). Furthermore, the results fall into or very close to the field for intermediate rocks.

Christiansen Feature and Bulk Mg/Si

Absolute element abundances are difficult to determine from mid-IR remote sensing data. Hence, we use the element ratio between Mg and Si for a correlation with the CF, as ratios of chemical data of two major elements is easier to extract from the space probe data (Fig.3b). In combination with the CF it provides a set of parameters relatively easily extracted from remote sensing data.

Here, our results fall along the area of synthetic Mercury composition glasses (Morlok et al., 2017a, 2020a). The terrestrial impact glasses and the refractory glass from laser-heated melting experiments (Morlok et al., 2020b) are clearly in a separate field compared to our samples relevant to Mercury. This

separation could help to identify glassy material formed in high-velocity impacts from such produced in volcanic processes.

Christiansen Feature and SCFM

The SCFM index expresses the degree of polymerization based on the $\text{SiO}_2/\text{SiO}_2+\text{CaO}+\text{FeO}+\text{MgO}$ relation (Salisbury and Walter, 1989). Similar to earlier studies, most of the results plot systematically below the terrestrial correlation line (Fig.4c). This could be related to the varying degrees of polymerization of the mixtures, however the correlation between glass content and SCFM is very weak ($R^2=0.04$) The results show similarities to the intermediate, basic and basaltic terrestrial rocks (Cooper et al., 2002)

4.3. Comparison with Remote Sensing Data of Mercury

Only few mid-infrared spectra are so far available for Mercury. Owing to technical reasons they cover larger surface regions ($10^4\text{--}10^6\text{ km}^2$) and offer only weak spectral contrast and low signal to noise ratios (Sprague et al., 2007). Therefore, we only use as an example the spectrum with the highest signal to noise for our comparisons. The spectrum integrates a region at about $210\text{--}250^\circ$ longitude and was obtained by the Mid Infrared Camera (MIRAC) at the Kitty Peak Observatory (Sprague et al., 2000).

The spectrum recalculated from emission (Fig.4) shows a CF at $8.5\text{ }\mu\text{m}$, three strong RBs at $9.3^\circ\mu\text{m}$, $9.9^\circ\mu\text{m}$, and $11^\circ\mu\text{m}$. A potential TF is visible at $12.4^\circ\mu\text{m}$. We compare it with our results of the 0-25 μm fraction of two mixtures reproducing some of the features.

The olivine-rich High-Mg Province mixture reproduces the CF of the hermean spectrum, and also has an RB at $9.4\text{ }\mu\text{m}$, near the $9.3\text{ }\mu\text{m}$ feature of the surface spectrum. A broad feature at $11^\circ\mu\text{m}$ overlaps with a (much narrower) band of the surface spectrum at the same position.

349 Plagioclase and enstatite-rich 357 High-Mg NVP mixture has a low-point at 8.5 μm , a strong RB at 9.4° μm
350 and a minor RB at 9.9° μm . These features are similar to the CF at 8.5 μm and the second and third RB
351 (9.3° μm and 9.9° μm) of the hermean sample.

352

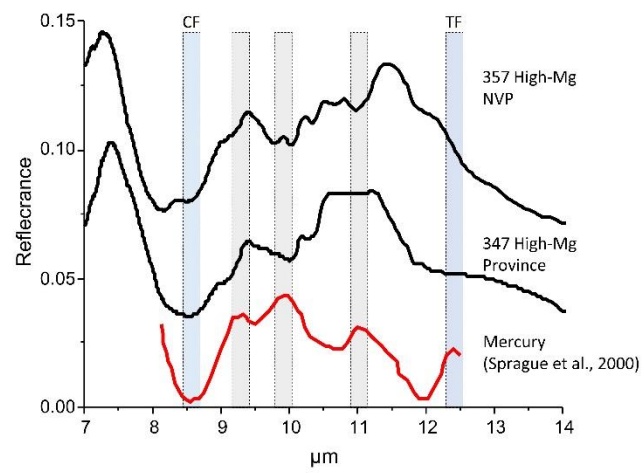


Figure 4

Figure 4. Comparison of Plagioclase and enstatite-rich High-Mg NVP, and olivine-rich High-Mg Province mixtures with a Mercury surface spectrum (recalculated from emissivity) (Sprague et al., 2000, 2007). Shaded areas mark characteristic features of the hermean spectrum.

5. Summary & Conclusions

We mixed bulk grain size fractions of analog materials relevant to the distinct terranes of Mercury. The powdered samples were analyzed in diffuse reflectance in the mid-infrared (2 μm – 20 μm).

The resulting spectra can be divided into three groups: (1) such as dominated by a single glass feature, (2) a group with forsterite, and (3) a group dominated by pyroxene bands. Plagioclase features, even when the phase is dominating the composition, are usually ‘overprinted’ by forsterite and pyroxene bands.

The spectral parameter CF in comparison with chemistry (SiO_2) and polymerization (SCFM) places the hermean mixtures mostly in the intermediate and basaltic range, similar to findings based in Peplowski and Stockstill-Cahill (2019). The correlation of parameters Mg/Si ratio and CF, that are easily obtainable in remote sensing, allows to distinguish materials that were formed by high energy evaporation processes in impacts from those formed by melting processes.

Preliminary comparison with a high-quality spectrum of the hermean surface (Sprague et al., 2000) show some similarity with band positions of lcp-HCT and High-Mg NVP mixtures, but none of our spectra is able to reproduce the remote sensing data entirely. This is not unexpected since further conditions (e.g. temperature) will also affect spectral properties, and this will have to be addressed by future studies.

Acknowledgements

A.M., M.P.R., A.N.S., I.W. and H.H. are supported by the DLR grant 50QW1701 and 50QW2201A1302. BC is a Research Associate of the Belgian Fund for Scientific Research-FNRS.

References

- Cartier, C., Wood, B.J. (2019) The Role of Reducing Conditions in Building Mercury. *Elements* 15, 39-45.
- Charlier, B., Grove, T.L., Zuber, M.T. (2013) Phase equilibria of ultramafic compositions on mercury and the origin of the compositional dichotomy. *Earth Planet. Sci. Lett.* 363, 50–60
- Christensen, P.R., Bandfield, J.L., Hamilton, V.E. (2001) Mars global surveyor thermal emission spectrometer experiment: investigation description and surface science results. *J. Geophys. Res.* 106 (E10), 23823–23872.
- Cooper, B.L., Salisbury, J.W., Killen, R.M., Potter, A.E. (2002) Midinfrared spectral features of rocks and their powders. *J. Geophys. Res.* 107 (E4), 5017–5
- Daly, T., Gavin, P., Chevrier, V. (2011) Effects of Thermal Alteration on the Near-Infrared and Mid-Infrared Spectra of Martian Phyllosilicates. 42nd Lunar and Planetary Science Conference, LPI Contribution No. 1608, p.1164
- Denevi, B.W., Ernst, C.M., Prockter, L.M., Robinson, M. S. (2020) The Geologic History of Mercury. In: Salomon, Nittler, Anderson (Eds.) *Mercury – The View after Messenger*. Cambridge.
- Donaldson Hanna, K. L., Greenhagen, B. T., Patterson, W. R., Pieters, C. M., Mustard, J. F., Bowles, N. E., Paige, D. A., Glotch, T. D., Thompson, C., Emery, J.P., Sprague, A.L., Witteborn, F.C., Colwell, F.C. (2007) Effects of varying environmental conditions on emissivity spectra of bulk lunar soils: Application to Diviner thermal infrared observations of the Moon. *Icarus* 283, 326-342.

401 Hapke, B. (1993) Theory of Reflectance and Emittance Spectroscopy. Cambridge Univ, Press, New York.

402 Hiesinger H., Helbert J., Mertis Co-I Team (2010) The Mercury Radiometer and Thermal Infrared
403 Spectrometer (MERTIS) for the BepiColombo mission. Planetary and Space Science 58, 144–165.

404 Hiesinger H, Helbert J, Alemanno G, Bauch KE, D’Amore M, Maturilli A, Morlok A, Reitze MP, Stangarone
405 C, Stojic AN, Varatharajan I, Weber I, the MC-IT (2020) Studying the Composition and Mineralogy of the
406 Hermean Surface with the Mercury Radiometer and Thermal Infrared Spectrometer (MERTIS) for the
407 BepiColombo Mission: An Update. Space Sci Rev 216(6):110 doi:10.1007/s11214-020-00732-4

408 Izenberg, N. R. et al. The low-iron, reduced surface of Mercury as seen in spectral reflectance by
409 MESSENGER. Icarus 228, 364–374 (2014).

410 McCubbin FM, Riner MA, Vander Kaaden KE, Burkemper LK (2012) Is Mercury a volatile-rich planet?
411 Geophysical Research Letters 39:L09202 doi:10.1029/2012GL051711

412 Van der Meer, F. (1995) Estimating and simulating the degree of serpentinization of peridotites using
413 hyperspectral remotely sensed imagery. Nonrenewable Resources 4, 84-98.

414 Morlok, A., Stojic, A., Dittmar, I., Hiesinger, H., Tiedeken, M., Sohn, M., Weber, I., Helbert, J. (2016a) Mid-
415 infrared spectroscopy of impactites from the Nördlinger Ries impact crater. Icarus 264, 352–368.

416 Morlok, A., Stojic, A., Weber, I., Hiesinger, H., Zanetti, M., Helbert, J. (2016b) Mid-infrared bi-directional
417 reflectance spectroscopy of impact melt glasses and tektites. Icarus 278, 162–179.

418 Morlok, A., Klemme, S., Weber, I., Stojic, A., Sohn, M., Hiesinger, H. (2017a) IR spectroscopy of synthetic
419 glasses with mercury surface composition: analogs for remote sensing. Icarus 296, 123–138.

420 Morlok, A., Klemme, S., Weber, I., Stojic, A., Sohn, M., Hiesinger, H., Helbert, J. (2020a) Mid-infrared
421 spectroscopy of planetary analogs: A database for planetary remote sensing. Icarus 324, 86–103.

422 Morlok, A., Hamann, C., Martin, D., Weber, I., Joy, K.H., Hiesinger, H., Wogelius, R., Stojic, A.N., Helbert, J.
423 (2020b) Mid-infrared spectroscopy of laser-produced basalt melts for remote sensing application. *Icarus*
424 335, 113410.

425 Morlok, A., Renggli, C., Charlier, B., Reitze, M. P., Klemme, S., Namur, O., Sohn, M. Martin, D., Weber, I.,
426 Stojic, A. N., Hiesinger, H., Joy, K. H., Wogelius, R., Tollan, P., Carli, C., Bauch, K. E., Helbert, J. (2021) Mid-
427 infrared reflectance spectroscopy of synthetic glass analogs for Mercury surface studies. *Icarus* 361,
428 114363.

429 Mustard, J.F., Hays, J.E. (1997) Effects of hyperfine particles on reflectance spectra from 0.3 to 25 μm .
430 *Icarus* 125, 145–163.

431 Namur, O., Charlier, B. (2017) Silicate mineralogy at the surface of mercury. *Nat. Geosci.* 10, 9–13.

432 Namur O, Collinet M, Charlier B, Grove TL, Holtz F, McCammon C (2016a) Melting processes and mantle
433 sources of lavas on Mercury. *Earth and Planetary Science Letters* 439:117-128

434 Namur O, Charlier B, Holtz F, Cartier C, McCammon C (2016b) Sulfur solubility in reduced mafic silicate
435 melts: Implications for the speciation and distribution of sulfur on Mercury. *Earth and Planetary Science*
436 *Letters* 448:102-11

437 Neumann, G. A. (2013) Bright and dark polar deposits on Mercury: Evidence for surface volatiles. *Science*
438 339, 296–300.

439 Nicodemus, F.E. (1965) Directional reflectance and emissivity of an opaque surface. *Appl. Opt.* 4, 767.

440 Nittler, L.R., Starr, R.D., Weider, S.Z., McCoy, T.J., Boynton, W.V., Ebel, D.S., Ernst, C.M., Evans, L.G.,
441 Goldsten, J.O., Hamara, D.K. (2011) The major-element composition of Mercury's surface from
442 MESSENGER X-ray spectrometry. *Science* 333,1847–1849.

443 Nittler LR, Frank EA, Weider SZ, Crapster-Pregont E, Vorburger A, Starr RD, Solomon SC (2020) Global
444 major-element maps of Mercury from four years of MESSENGER X-Ray Spectrometer observations.
445 Icarus 345:113716 doi:<https://doi.org/10.1016/j.icarus.2020.113716>

446 Peplowski PN, Lawrence DJ, Feldman WC, Goldsten JO, Bazell D, Evans LG, Head JW, Nittler LR, Solomon
447 SC, Weider SZ (2015) Geochemical terranes of Mercury's northern hemisphere as revealed by
448 MESSENGER neutron measurements. Icarus 253:346-363
449 doi:<http://dx.doi.org/10.1016/j.icarus.2015.02.002>

450 Peplowski PN, Evans LG, Hauck SA, McCoy TJ, Boynton WV, Gillis-Davis JJ, Ebel DS, Goldsten JO, Hamara
451 DK, Lawrence DJ, McNutt RL, Nittler LR, Solomon SC, Rhodes EA, Sprague AL, Starr RD, Stockstill-Cahill KR
452 (2011) Radioactive elements on Mercury's surface from MESSENGER: Implications for the planet's
453 formation and evolution. Science 333(6051):1850-1852 doi:10.1126/science.1211576

454 Peplowski, P.N., Stockstill-Cahill, K. (2019) Analytical identification and characterization of the major
455 geochemical Terranes of Mercury's northern hemisphere. J. Geophys. Res. 124, 2414–2429.

456 Peplowski, P. N. (2016) Remote sensing evidence for an ancient carbon-bearing crust on Mercury. Nat.
457 Geosci. 9, 273–276 .

458 Renggli, C. J., Klemme, S., Morlok, A., Berndt, J., Weber, I., Hiesinger, H., King, P. L. (2022) Sulfides and
459 hollows formed on Mercury's surface by reactions with reducing S-rich gases. Earth and Planetary
460 Science Letters 593, 117647.

461 Reitze M. P. Weber I., Morlok A., Hiesinger H., Bauch K. E., Stojic A. N., Helbert J. (2020) Mid-infrared
462 spectroscopy of crystalline plagioclase feldspar samples with various Al,Si order and implications for
463 remote sensing of Mercury and other terrestrial Solar System objects. EPSL 554, 116697.

464 Reitze, M. P., Weber, I., Morlok, A., Hiesinger, H., Bauch, K. E., Stojic, A. N., Helbert, J. (2021) Mid-
465 Infrared Spectroscopy of Anorthosite Samples From Near Manicouagan Crater, Canada, as Analogue for

466 Remote Sensing of Mercury and Other Terrestrial Solar System Objects. *Journal of Geophysical Research:*
 467 *Planets*, 126, e06832

468 Rothery DA, Massironi M, Alemanno G, Barraud O, Besse S, Bott N, Brunetto R, Bunce E, Byrne P,
 469 Capaccioni F, Capria MT, Carli C, Charlier B, Cornet T, Cremonese G, D'Amore M, De Sanctis MC,
 470 Doressoundiram A, Ferranti L, Filacchione G, Galluzzi V, Giacomini L, Grande M, Guzzetta LG, Helbert J,
 471 Heyner D, Hiesinger H, Hussmann H, Hyodo R, Kohout T, Kozyrev A, Litvak M, Lucchetti A, Malakhov A,
 472 Malliband C, Mancinelli P, Martikainen J, Martindale A, Maturilli A, Milillo A, Mitrofanov I, Mokrousov M,
 473 Morlok A, Muinonen K, Namur O, Owens A, Nittler LR, Oliveira JS, Palumbo P, Pajola M, Pegg DL, Penttilä
 474 A, Poli R, Quarati F, Re C, Sanin A, Schulz R, Stangarone C, Stojic A, Tretiyakov V, Väisänen T,. (2020)
 475 Rationale for BepiColombo Studies of Mercury's Surface and Composition. *Space Science Reviews* 216,
 476 .66.

477 Salisbury, J.W., Walter, L.S., Vergo, N., D'Aria, D.M. (1991°) *Infrared (2,1-25 µm) Spectra of Minerals.*
 478 Johns Hopkins University Press, Baltimore, MD.

479 Salisbury, J.W. (1993) *Mid-infrared spectroscopy: laboratory data.* In: Pieters, C.M., Englert, P.A.J. (Eds.),
 480 *Remote Geochemical Analysis: Elemental and Mineralogical Composition.* Cambridge University Press.

481 Salisbury, J.W., Wald, A., Di Aria, D.M. (1994) *Thermal-infrared remote sensing and Kirchhoff's law 1.*
 482 *Labaratory measurements. J. Geophys. Res.* 99 (B6), 11897–11911.

483 Salisbury, J.W., Walter, L.S. (1989) *Thermal Infrared (2.5-13.5 µm) Spectroscopic Remote Sensing of*
 484 *Igneous Rock Types on Particulate Planetary Surfaces. Journal of Geophysical Research* 94, 9192-9202.

485 Sprague, A.L., Kozlowski, R.W.H., Wittebom, F.C., et al. (1994) *Mercury: evidence for anorthosite and*
 486 *basalt from mid-infrared (7.5–13.5 micrometer) spectroscopy. Icarus* 109, 156–167.

487 Sprague, A., Deutsch, L.K., Hora, J., Fazio, G.G., Ludwig, B., Emery, J., Hoffmann, W.F. (2000) *Mid-infrared*
 488 *(8.1–12.5 µm) imaging of Mercury. Icarus* 147, 421–432.

489 Sprague, A.L., Emery, J.P., Donaldson, K.L., Russell, R.W., Lynch, D.K., Mazuk, A.L. (2002) Mercury: mid-
490 infrared (3-13.5 μm) observations show heterogeneous composition, presence of intermediate and basic
491 soil types, and pyroxene. *Meteoritics Planet. Sci.* 37, 1255–1268.

492 Sprague, A., Warell, J., Cremonese, G., Langevin, Y., Helbert, J., Wurz, P., Veselovsky, I., Orsini, S., Milillo,
493 A. (2007) Mercury's surface composition and character as measured by ground-based observations.
494 *Space Sci. Rev.* 132, 399–431.

495 Sprague, A.L., Roush, T.L. (1998) Comparison of laboratory emission spectra with mercury telescopic
496 data. *Icarus* 133, 174–183.

497 Sprague, A. L., Donaldson Hanna, K. L., Kozlowski, R. W. H., Helbert, J., Maturilli, A., Warell, J. B., Hora, J.
498 L. (2009) Spectral emissivity measurements of Mercury's surface indicate Mg- and Ca-rich mineralogy, K-
499 spar, Na-rich plagioclase, rutile, with possible perovskite, and garnet. *Planetary and Space Science* 57,
500 364-383.

501 Stockstill-Cahill, K. R., McCoy, T. J., Nittler, L. R., Weider, S. Z., Hauck, S. A. (2012) Magnesium-rich
502 crustal compositions on Mercury: Implications for magmatism from petrologic modeling. *Journal of*
503 *Geophysical Research* 117, CiteID E00L15.

504 Vander Kaaden, K.E., McCubbin, F.M., Nittler, L.R., Peplowski, P.N., Weider, S.Z., Frank, E.A., McCoy, T.
505 (2017) Geochemistry, mineralogy, and petrology of Boninitic and Komatiitic rocks on the Mercurian
506 surface: insights into the Mercurian mantle. *Icarus*. <https://doi.org/10.1016/j.icarus.2016.11.041>. in
507 Press.

508 Vander Kaaden, K. E., McCubbin, F.M. (2016) The origin of boninites on Mercury: An experimental study
509 of the northern volcanic plains lavas. *Geochimica et Cosmochimica Acta* 173, 246-263.

510 Thomson, J.L., Salisbury, J.W. (1993) The mid-infrared reflectance of mineral mixtures (7–14 microns).
511 *Remote Sens. Environ.* 45, 1–13.

512 Vilas, F. (2016) Mineralogical indicators of Mercury's hollows composition in MESSENGER color
513 observations. *Geophys. Res. Lett.* 43, 1450–1456.

514 Weber I., Reitze M.P., Heeger M., Adolphs T., Morlok A., Stojic A.N., Hiesinger H., Arlinghaus H.F., Helbert
515 J. (2021) The effect of excimer laser irradiation on mid-IR spectra of mineral mixtures for remote sensing.
516 *EPS*: 569, 117072.

517 Weber, I.; Morlok, A.; Bischoff, A.; Hiesinger, H.; Ward, D.; Joy, K. H.; Crowther, S. A.; Jastrzebski, N. D.;
518 Gilmour, J. D.; Clay, P. L.; Wogelius, R. A.; Greenwood, R. C.; Franchi, I. A.; Münker, C. (2016)
519 Cosmochemical and spectroscopic properties of Northwest Africa 7325—A consortium study.
520 *Meteoritics & Planetary Science* 51, 3-30.

521 Weber, I., Morlok, A., Grund, T., Bauch, K. E., Hiesinger, H., Stojic, A., & Joy, K. H. (2018). A mid-infrared
522 reflectance database in preparation for space missions. In *Lunar and planetary science conference* (p.
523 1430).

524 Weider, S. Z., Nittler, L. R., Starr, R. D., Ellen, Crapster-Pregont, Peplowski, P. N., Denevi, B. W., Head, J.
525 W., Byrne, P. K., Hauck, S. A., Ebel, D. S., Solomon, S. C. (2015). Evidence for geochemical terranes on
526 mercury: global mapping of major elements with MESSENGER's X-ray spectrometer. *Earth Planet. Sci.*
527 *Lett.* 416, 109–120.

528

529

530

531

532

533

Smooth Plains	CF									
ID 343										
0-25 μm	8.04	9.01	9.63	9.92	10.20	10.54	10.82		11.65	15.69
25-63 μm	7.93		9.51	9.92	10.23	10.49	10.78	11.27		15.77
63-125 μm	7.90		9.40	9.91	10.23	10.49	10.78			15.76
125-250 μm	7.84		9.62	9.89	10.21	10.46				15.69
ID 344										
0-25 μm	7.91		9.54	9.87	10.18	10.51			11.67	14.43
25-63 μm	7.89		9.53	9.90	10.18	10.48		11.28	13.75	14.43
63-125 μm	7.84		9.51	9.89	10.20	10.48		11.30		14.47
125-250 μm	7.83		9.51	9.91	10.22	10.45	10.76	11.06	11.38	13.79
ID 345										
0-25 μm	7.97		9.59		10.16	10.56		11.42	11.75	15.81
25-63 μm	7.93		9.58		10.17	10.55				15.85
63-125 μm	7.91		9.61		10.16	10.50				15.78
125-250 μm	7.89		9.59		10.17	10.56				15.96
ID 174										
0-25 μm	7.89		9.58						11.78	
25-63 μm	7.87		9.58							
63-125 μm	7.91		9.58							
125-250 μm	7.91		9.58							
High-Mg Province										
ID 346										
0-25 μm	8.60		9.37		10.19	10.64				14.12
25-63 μm	7.91		9.37		10.19	10.57		11.21	11.92	14.84
63-125 μm	7.81		9.36		10.19	10.56	10.80		11.90	14.85
125-250 μm	7.77		9.36			10.55	10.81		12.41	14.86
ID 347										
0-25 μm	8.53		9.39		10.18	10.64	10.84			14.10
25-63 μm	8.03		9.38		10.19	10.57	10.79		11.90	15.91
63-125 μm	7.87		9.38		10.18	10.57	10.79		11.92	15.81
125-250 μm	7.83		9.37		10.18	10.56	10.79		11.92	15.81
ID 348										
0-25 μm	8.21		9.63		10.16	10.64			11.96	15.96
25-63 μm	8.14		9.56		10.16	10.59			11.92	15.94
63-125 μm	8.11		9.66		10.18	10.57			11.89	15.98
125-250 μm	8.08		9.61		10.17	10.56			11.89	15.89
ID 338										
0-25 μm	8.27			9.90					12.06	
25-63 μm	8.21			9.84						
63-125 μm	8.22			9.90						
125-250 μm	8.20			9.87						

Low-Mg NVP	CF									
ID 349										
0-25 µm	7.88		9.45		10.16	10.56		11.62		15.66
25-63 µm	7.85		9.40		10.16	10.52				15.79
63-125 µm	7.80		9.39		10.16	10.48				15.71
125-250 µm	7.76		9.39		10.15	10.50				15.82
ID 350										
0-25 µm	8.14	8.36	9.40	9.89		10.62		11.32	11.50	15.73
25-63 µm	7.86		9.36	9.89		10.52	10.82			15.77
63-125 µm	7.82		9.36	9.91		10.52	10.81			15.77
125-250 µm	7.76		9.39	9.89	10.19	10.52				15.93
ID 174										
0-25 µm	7.89		9.58						11.78	
25-63 µm	7.87		9.58							
63-125 µm	7.91		9.58							
125-250 µm	7.91		9.58							
IcP-HCT										
ID 351										
0-25 µm	8.15		9.63		10.15	10.61		11.94		16.12
25-63 µm	8.09		9.62		10.15	10.55		11.91		15.95
63-125 µm	8.04		9.68		10.16	10.55				15.95
125-250 µm	8.02		9.57		10.16	10.59		11.92		15.91
ID 352										
0-25 µm	8.14		9.54		10.16	10.64		11.30	11.90	15.92
25-63 µm	7.87		9.48		10.16	10.58				15.91
63-125 µm	7.83		9.44		10.16	10.55			11.91	15.91
125-250 µm	7.79		9.39		10.16	10.55			11.90	15.91
ID 353										
0-25 µm	8.15		9.66		10.16	10.62		11.24	11.92	16.01
25-63 µm	7.98		9.52		10.18	10.57			11.90	15.90
63-125 µm	7.86		9.53		10.18	10.57			11.90	15.94
125-250 µm	7.80		9.46		10.16	10.57			11.93	15.90
ID 354										
0-25 µm	8.18	8.34	9.46	9.93	10.18	10.72			12.14	16.01 16.47
25-63 µm	7.89		9.48		10.18	10.56			11.92	15.96 16.35
63-125 µm	7.85		9.39	9.91	10.18	10.54			11.91	15.88 16.49
125-250 µm	7.75		9.39		10.18	10.55				15.88 16.48
ID 181										
0-25 µm	8.08			9.80					11.91	
25-63 µm	8.07			9.80						
63-125 µm	8.06			9.78						
125-250 µm	8.04			9.81						

High-Mg NVP	CF											
ID 355												
0-25 μm	8.08			9.83		10.48			11.86			
25-63 μm	8.06			9.74		10.50						
63-125 μm	8.04			9.79		10.50						
125-250 μm	8.05			9.79								
ID 356												
0-25 μm	8.08		9.42	9.89	10.23	10.51	10.79		11.43		14.42	
25-63 μm	7.96		9.48	9.89	10.20	10.51			11.30		14.43	15.74
63-125 μm	7.87		9.42	9.89	10.24	10.49					14.42	15.78
125-250 μm	7.86		9.39	9.89		10.51	10.79				14.42	15.74
ID 357												
0-25 μm	8.15	8.38	9.39	9.90	10.23	10.52	10.79		11.44		14.41	15.73
25-63 μm	7.89		9.42	9.91	10.21	10.53	10.77		11.33		14.42	17.46
63-125 μm	7.83		9.40	9.91	10.22	10.46	10.79		11.34	13.77	14.48	15.63
125-250 μm	7.81		9.37	9.91	10.21	10.49	10.79		11.34	13.77	14.48	15.70
ID 181												
0-25 μm	8.08			9.80					11.91			
25-63 μm	8.07			9.80								
63-125 μm	8.06			9.78								
125-250 μm	8.04			9.81								

Table 4. Band positions of the studied mixtures. In Bold: position of the CF of the respective grain size fractions. (In μm).

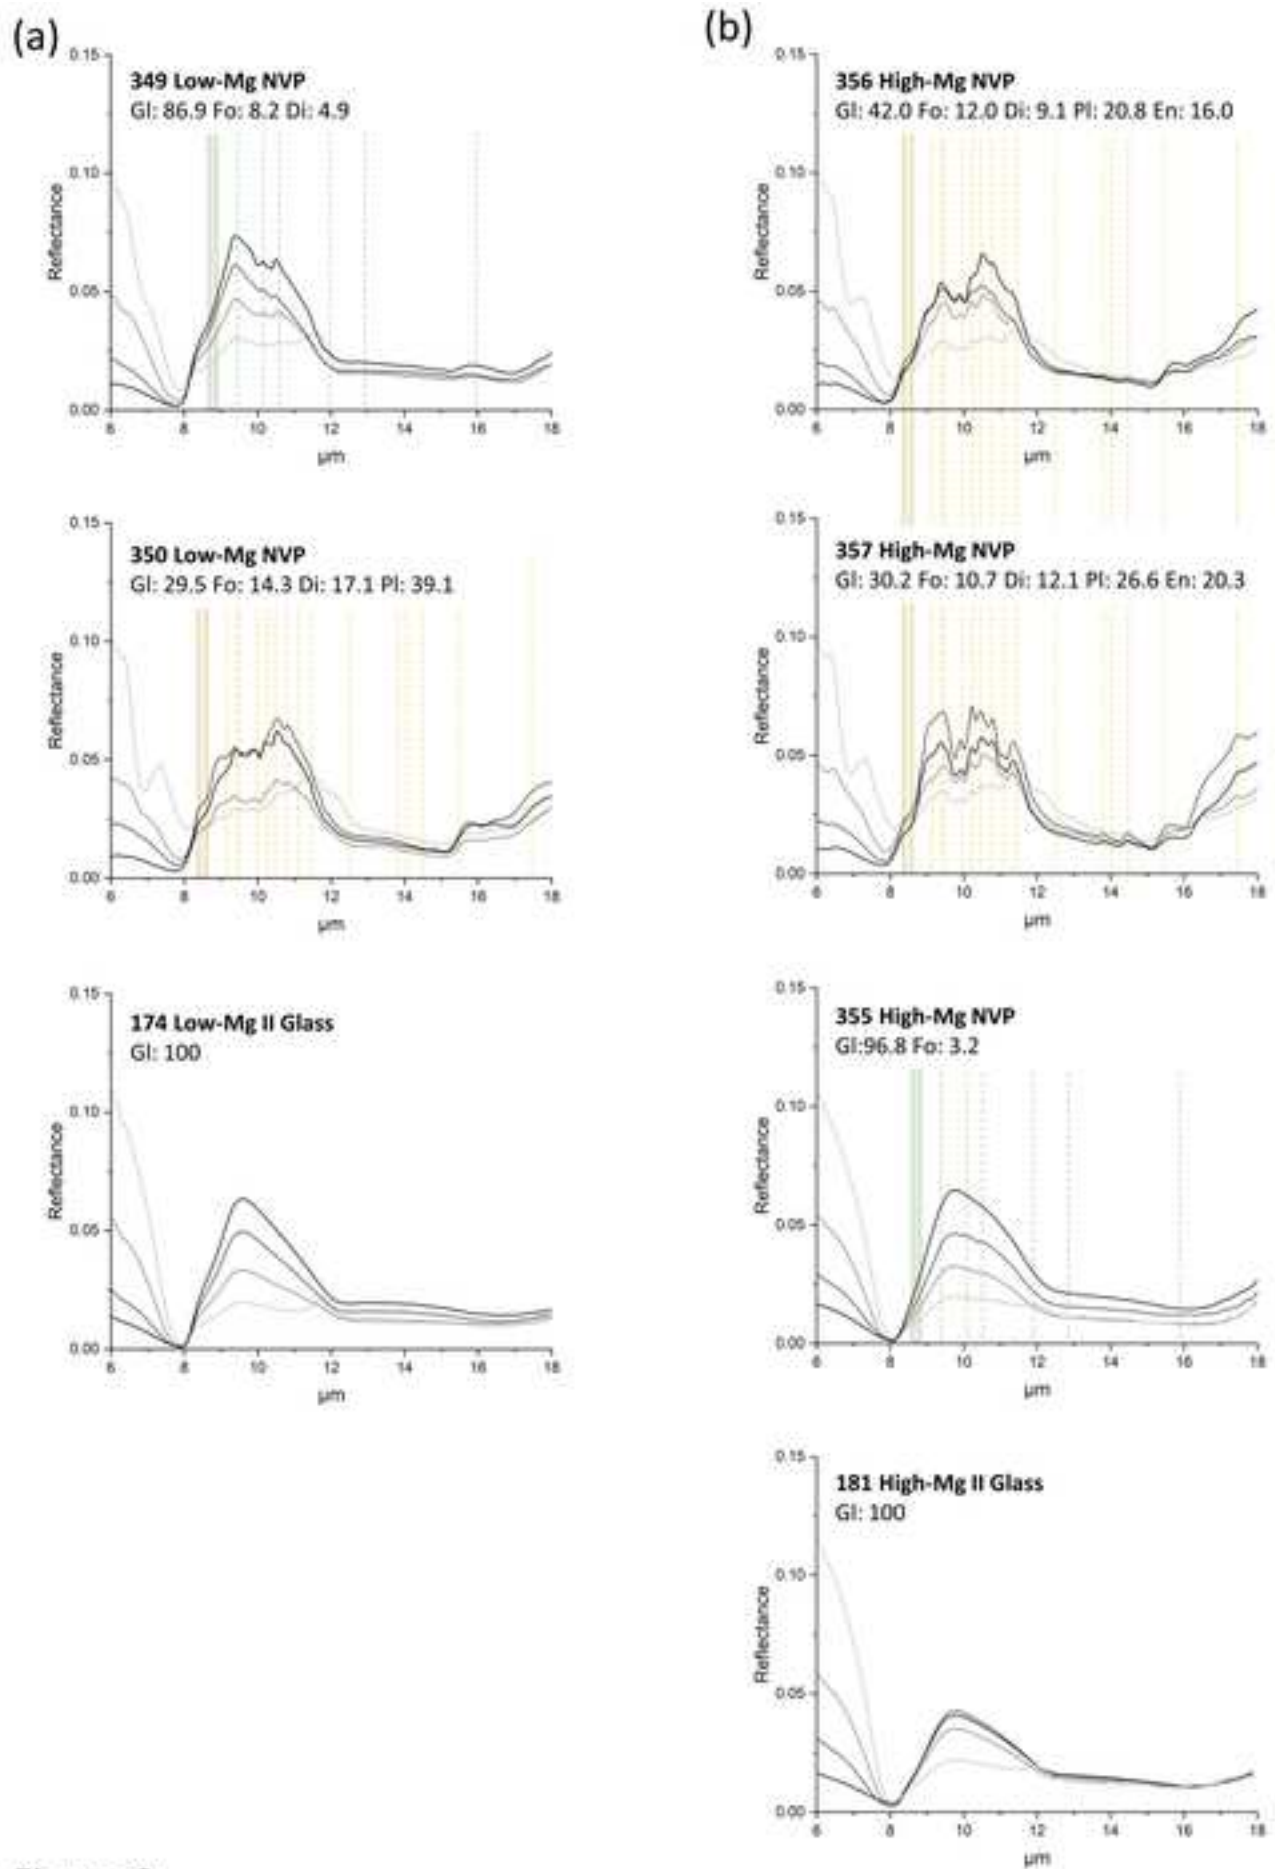


Figure 2

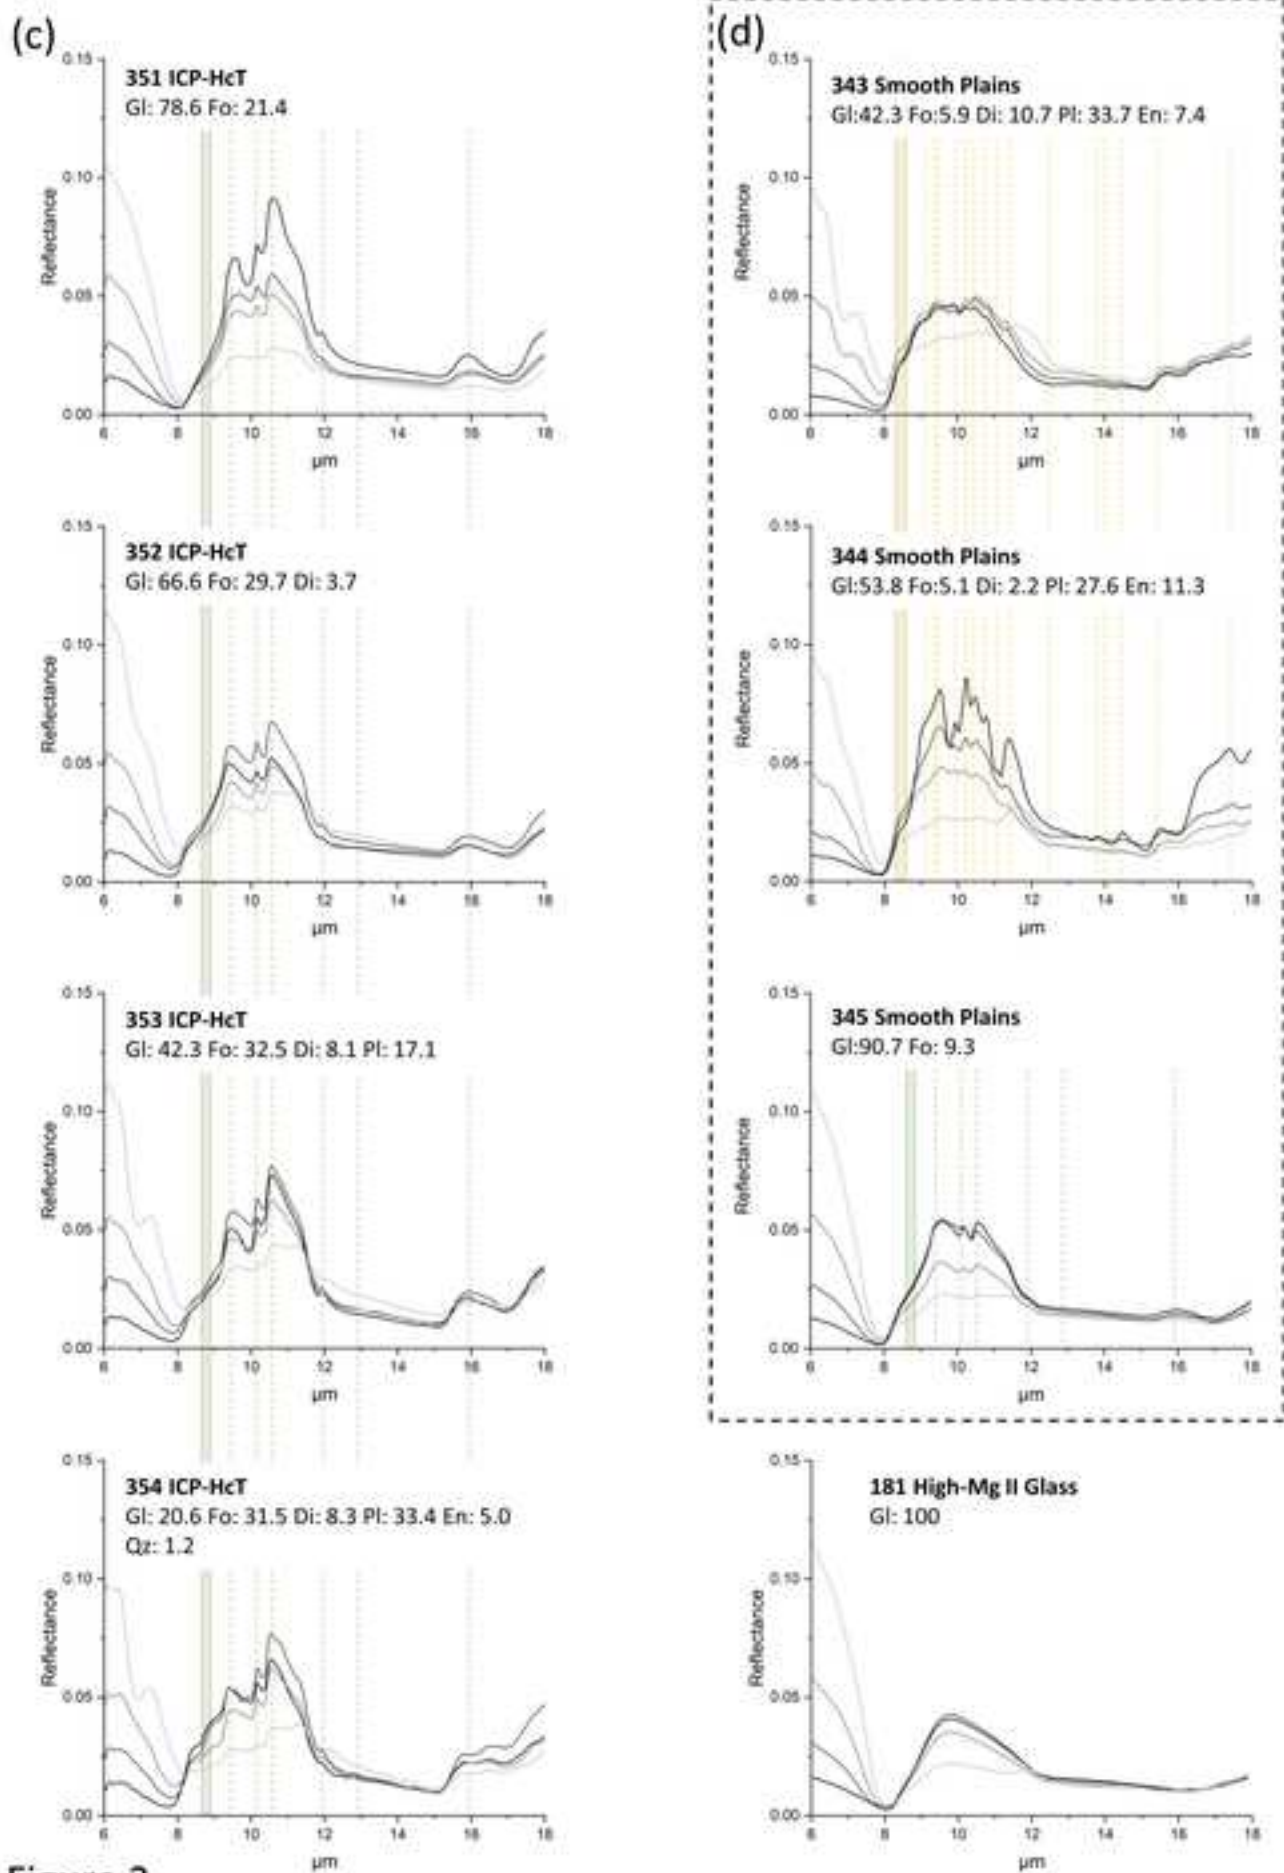


Figure 2

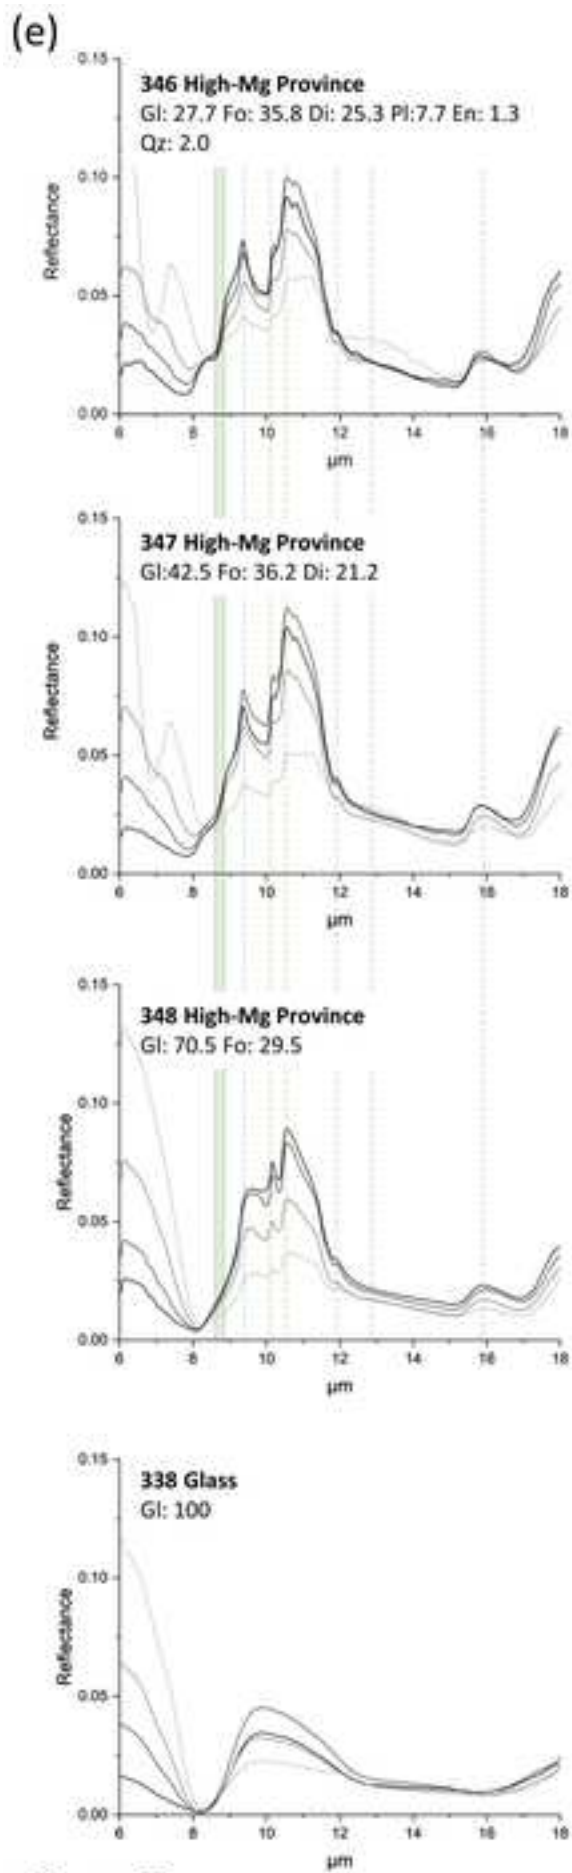


Figure 2

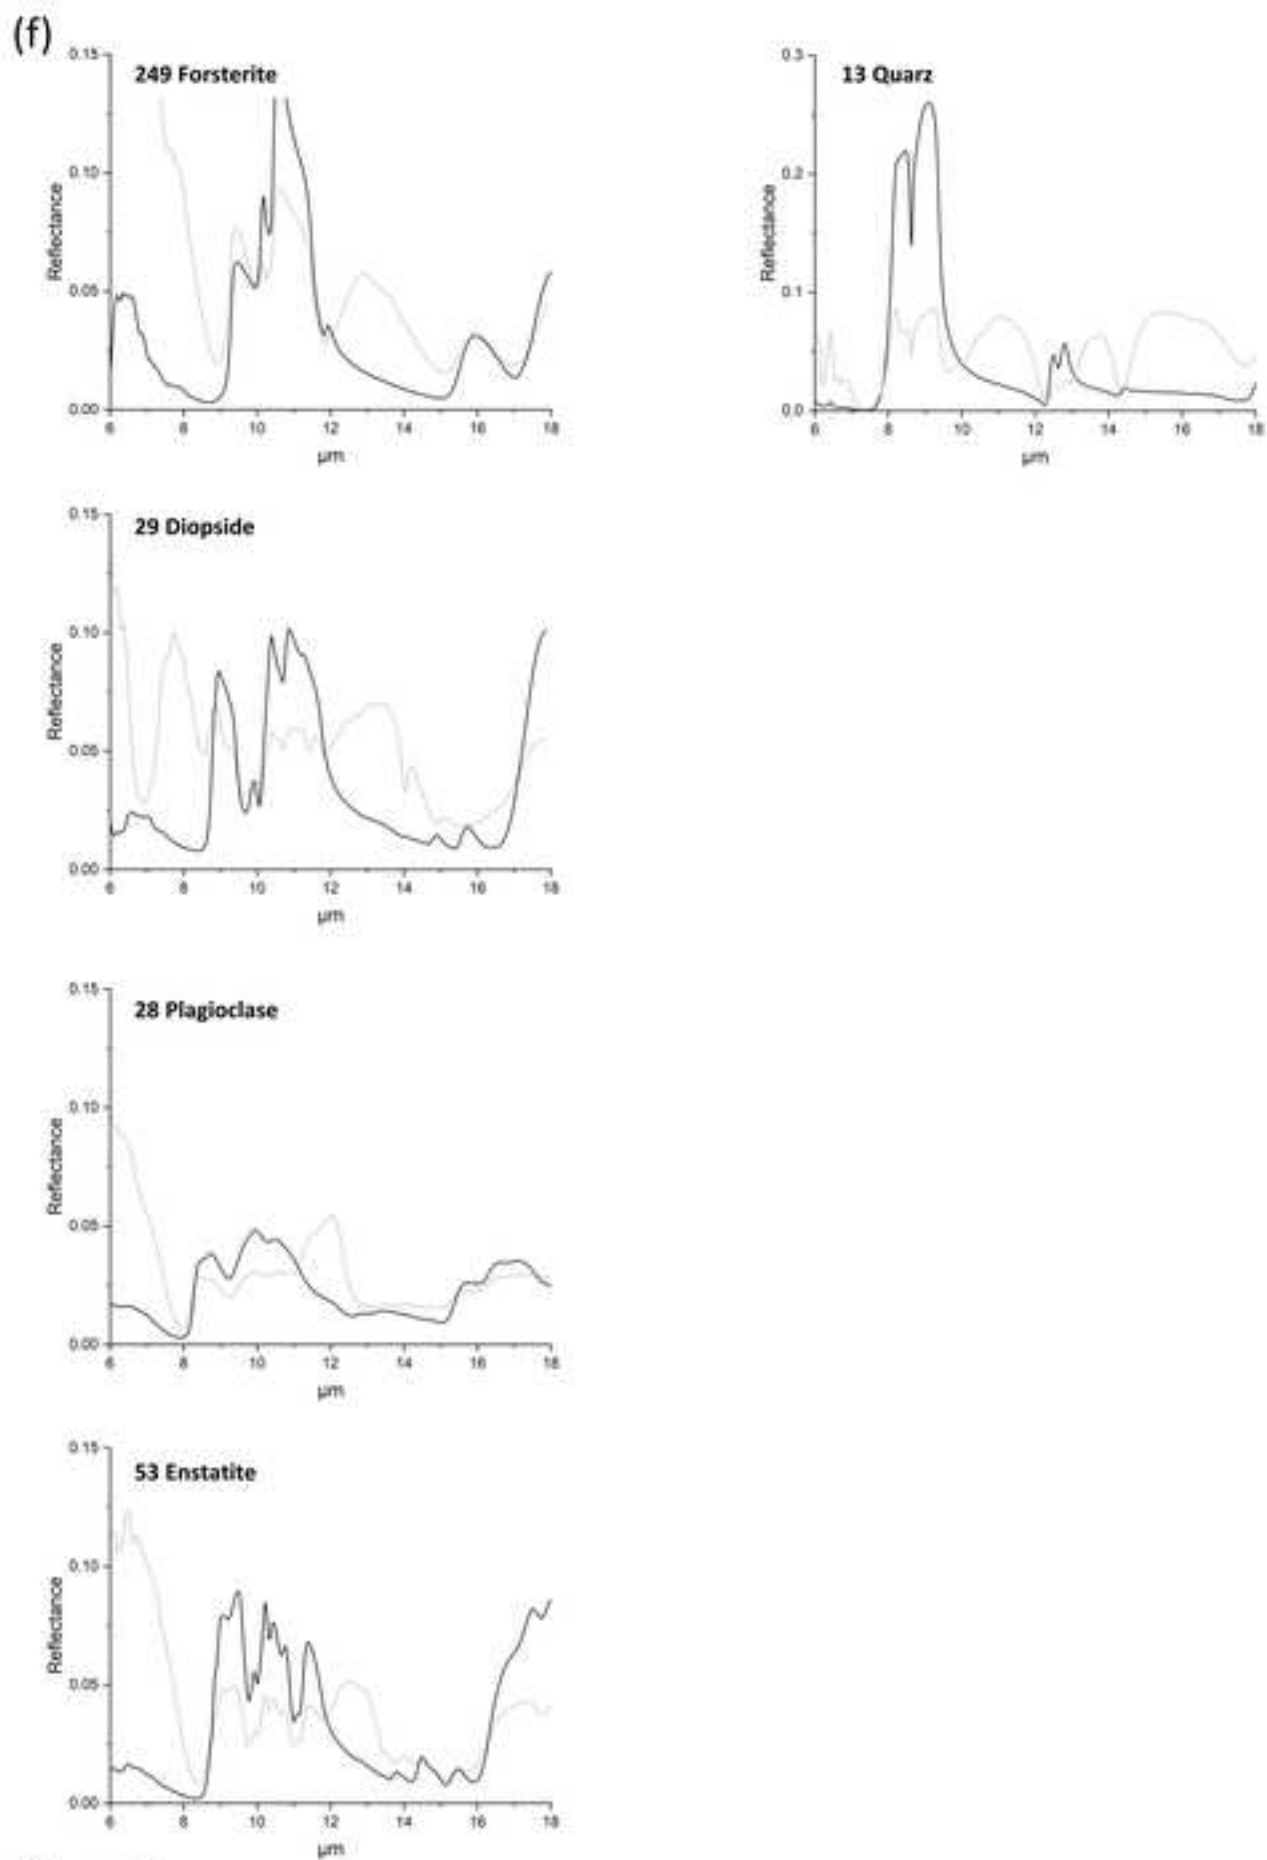


Figure 2

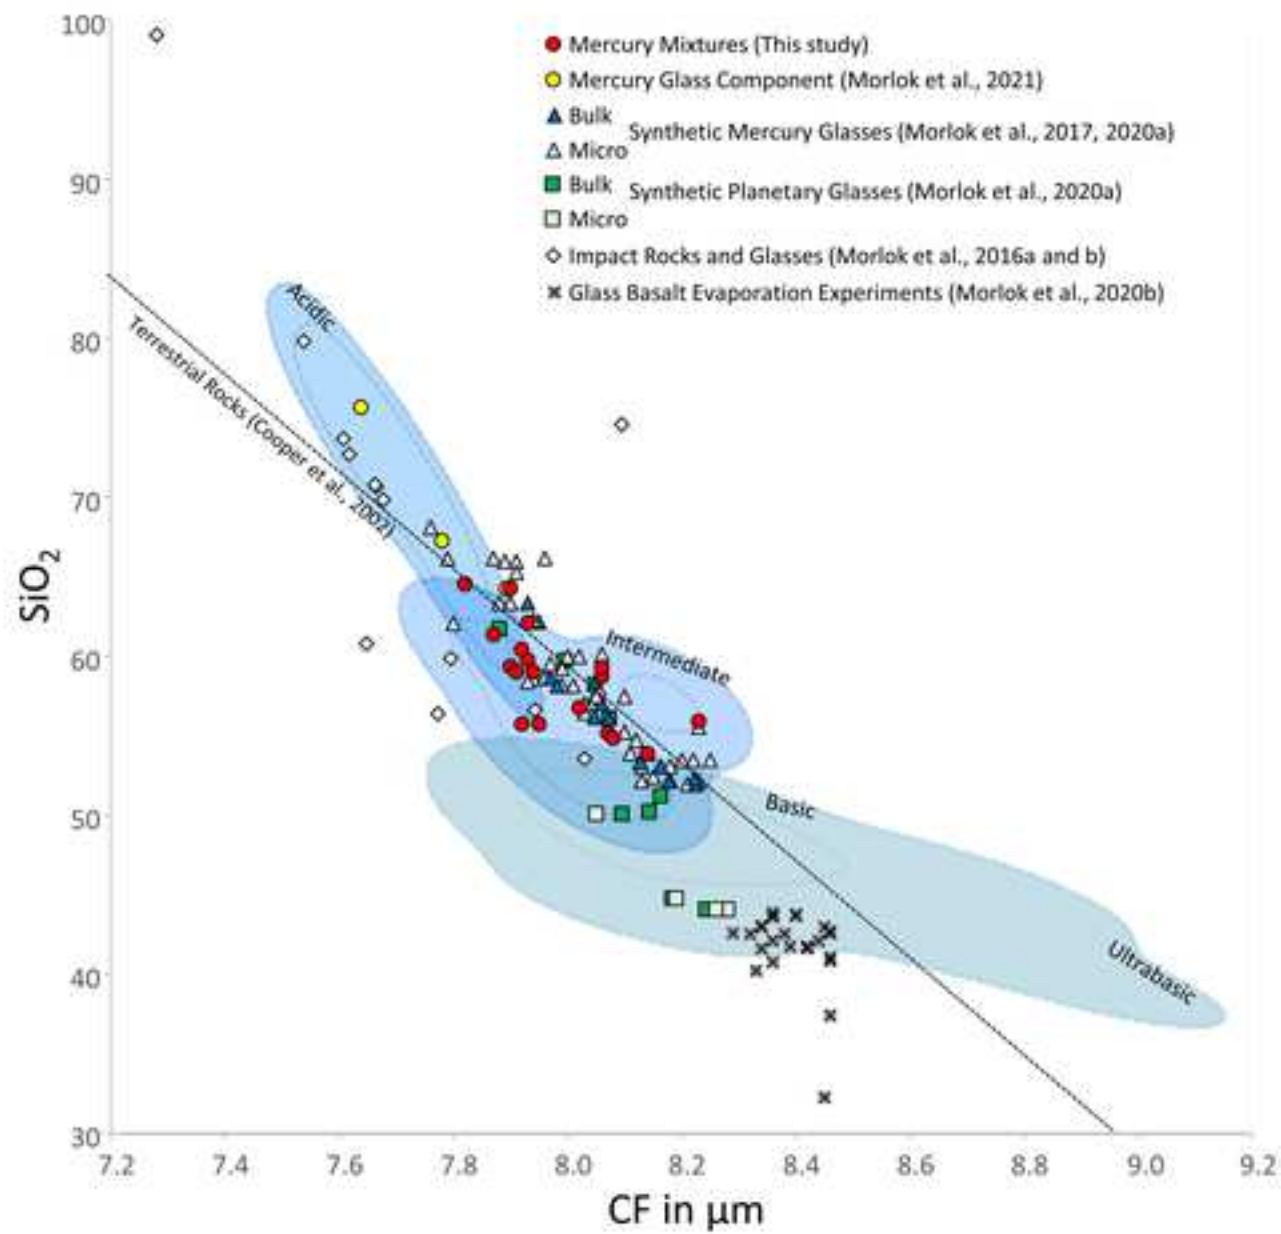


Figure 3a

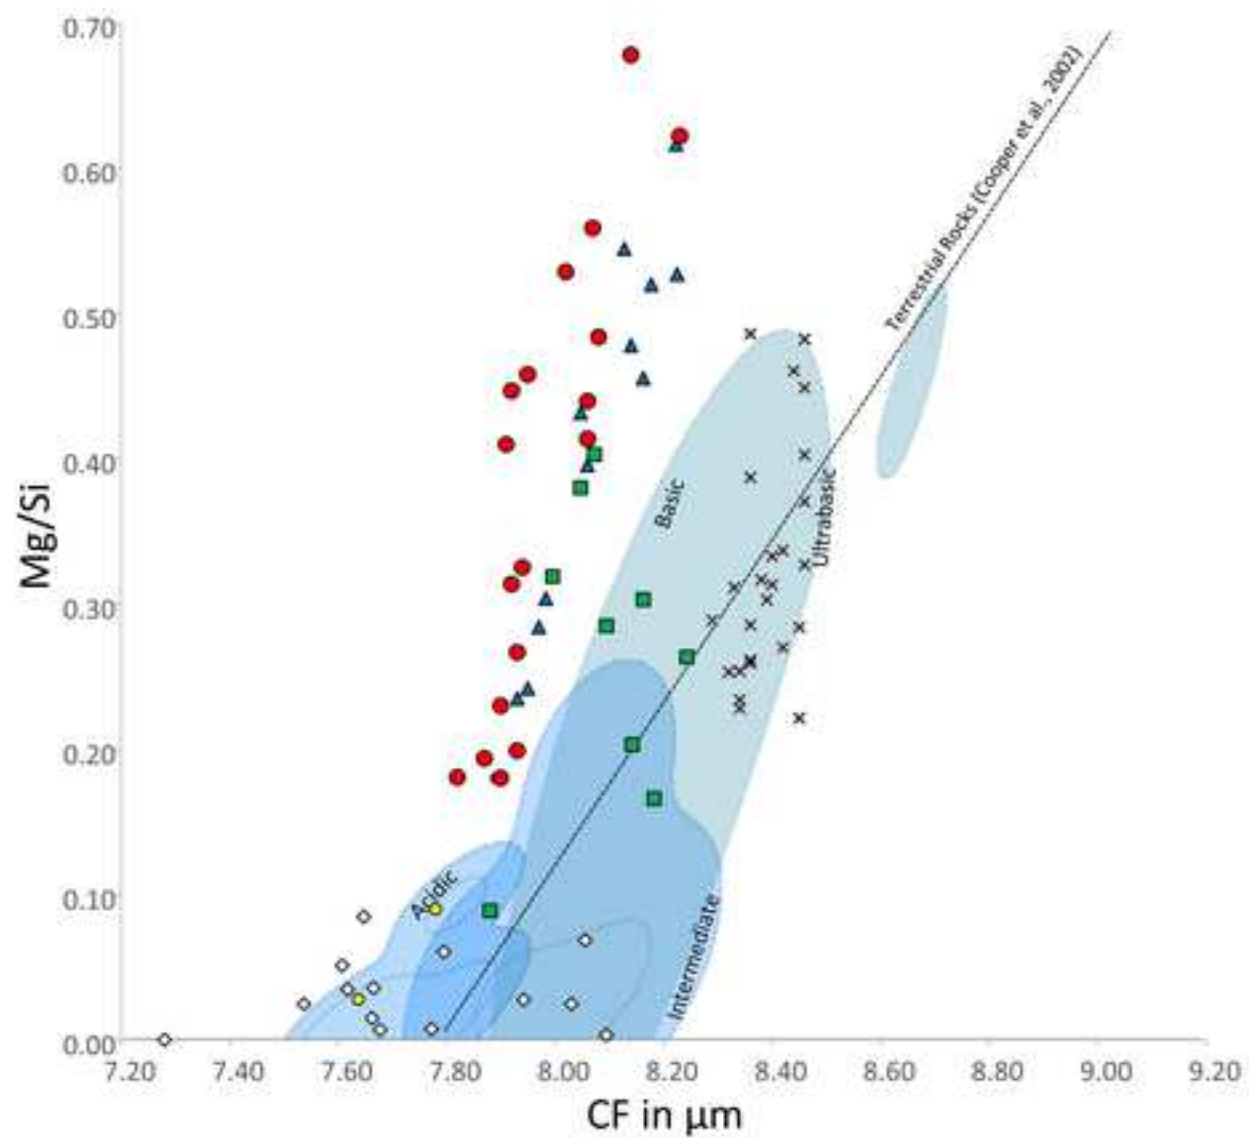


Figure 3b

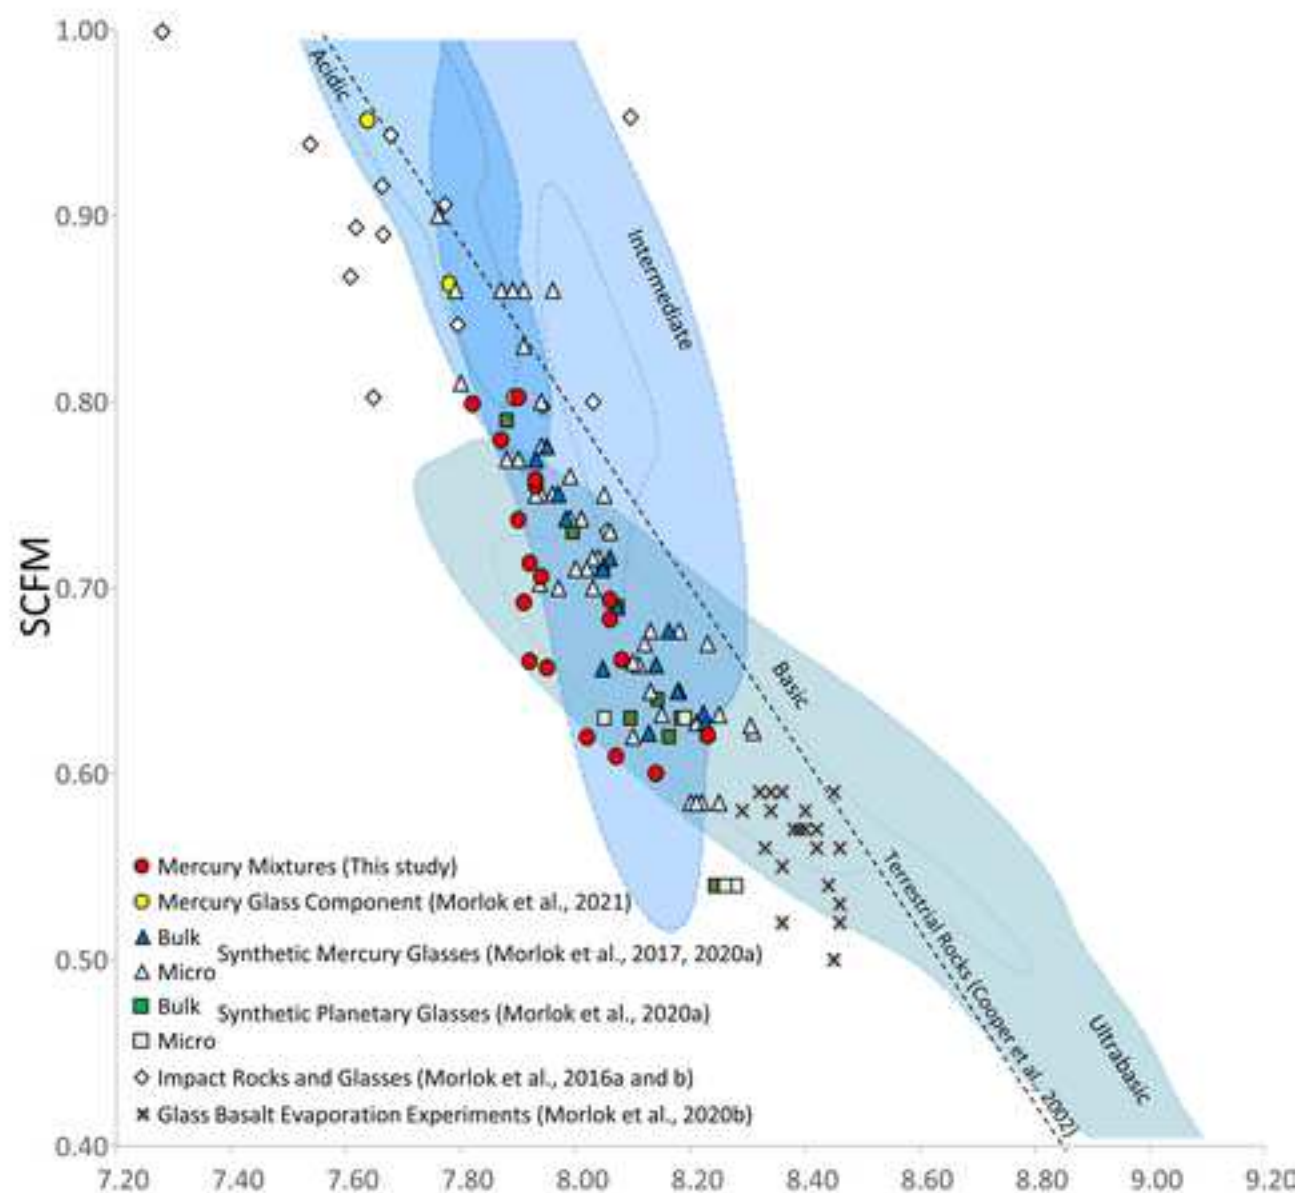


Figure 3c

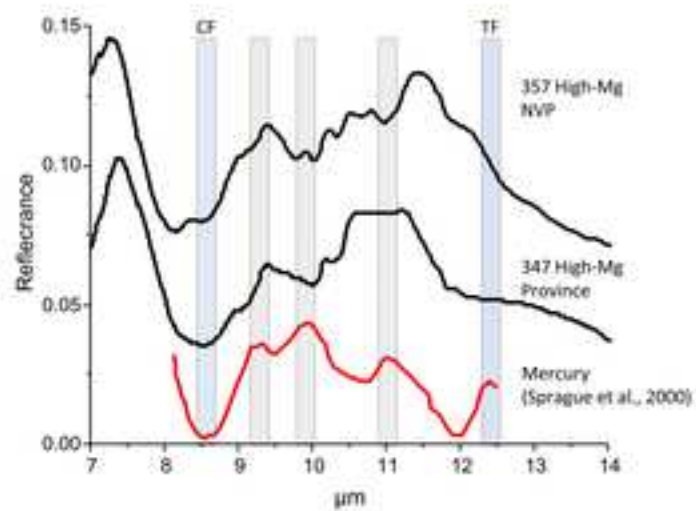


Figure 4

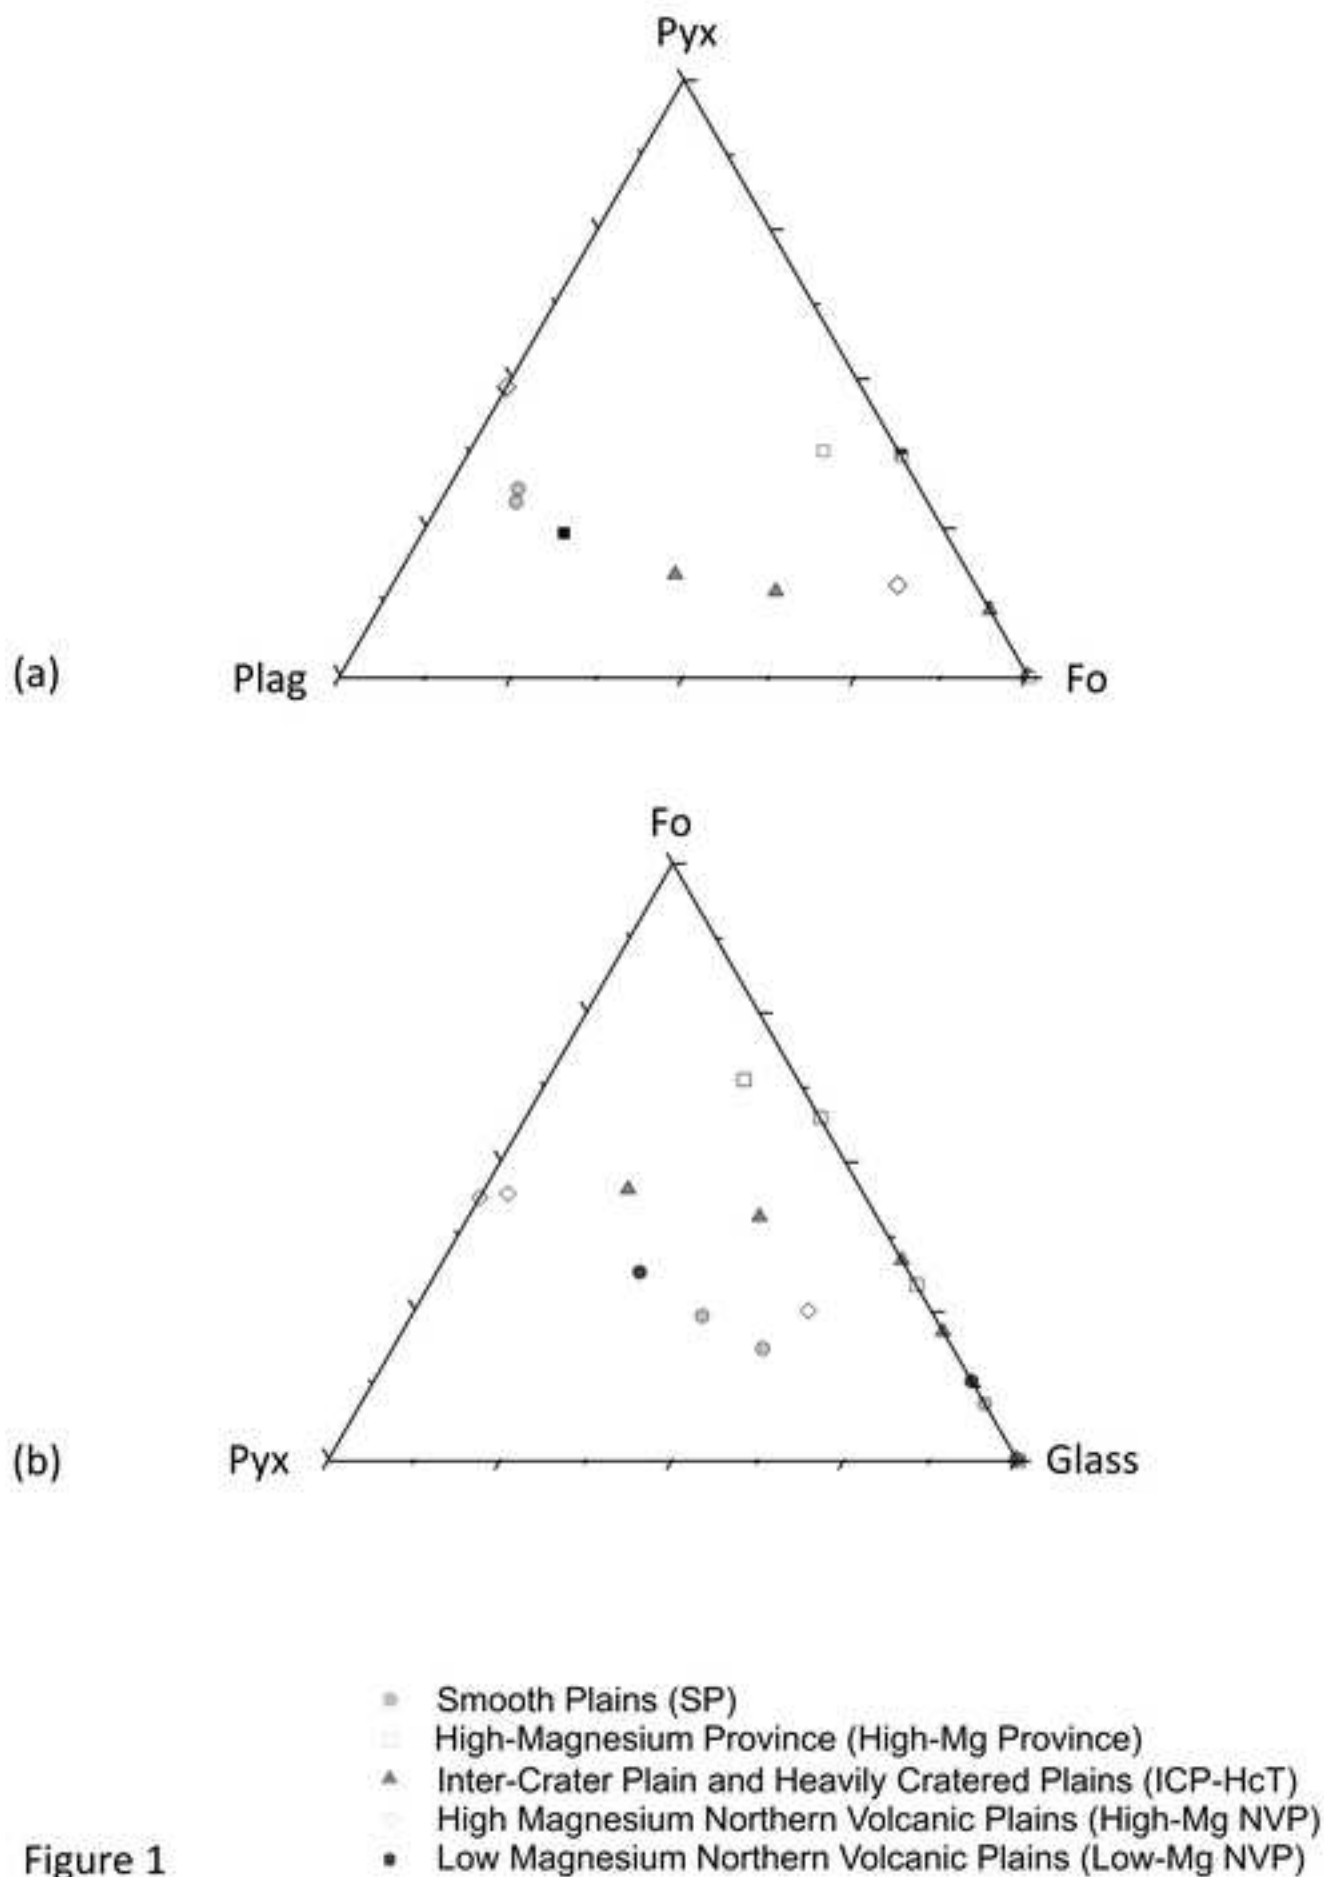


Figure 1